

A Deeper Understanding of Interstitial Boron-Doped Anatase Thin Films as A Multifunctional Layer Through Theory and Experiment

Miguel Quesada-Gonzalez,^a Benjamin A. D. Williamson,^{a,c} Carlos Sotelo-Vazquez,^a Andreas Kafizas,^e Nicolas D. Boscher,^b Raul Quesada-Cabrera,^a David O. Scanlon^{a,c,d}, Claire J. Carmalt^a and Ivan P. Parkin.^{a*}

^a Department of Chemistry, Christopher Ingold Building, University College London, 20 Gordon Street, London WC1H 0AJ, UK.

^b Department of Materials Research and Technology, Luxembourg Institute of Science and Technology, 5 Avenue des Hauts-Fourneaux, Esch-sur-Alzette, L-4362, Luxembourg.

^c Thomas Young Centre, University College London, Gower Street, London WC1E 6BT, United Kingdom.

^d Diamond Light Source Ltd., Diamond House, Harwell Science and Innovation Campus, Didcot, Oxfordshire OX11 0DE, UK.

^e Department of Chemistry, Imperial College London, London SW7 2AZ, U.K.

ABSTRACT: Thin films of interstitial boron-doped anatase TiO₂, with varying B concentrations, were deposited via one-step atmospheric pressure chemical vapour deposition (APCVD) on float glass substrates. The doped films showed a remarkable morphology and enhanced photoactivity when compared to their undoped analogues. The TiO₂:B films also presented enhanced conductivity and electron mobility as measured by Hall Effect probe as well as a high adherence to the substrate, stability and extended lifetime. The structure and composition of the different samples of TiO₂:B films were studied by X-ray Diffraction (XRD), Raman spectroscopy, Scanning Electron Microscopy (SEM) and Dynamic Secondary Ion Mass Spectrometry (D-SIMS). Hybrid density functional theory was used to explore the defect chemistry of B-doped anatase and to understand the experimental results.

1. Introduction

Among all known photocatalytic materials, titanium dioxide (TiO₂) has been the most extensively studied photocatalytic material due to its multifunctional applications from desirable properties.¹ There has been a large research drive into the degradation of organic pollutants leading to the industrial use of TiO₂ for the production of environmental, self-cleaning and photocatalytic technologies such as the Pilkington Activ™ glass. In the last few decades, strenuous efforts have been made combining theory and experiment to fully understand the mechanisms of photocatalysis in TiO₂ polymorphs.^{2,3}

TiO₂ has been synthesised using a wide range of synthetic methods, including sol-gel,⁴ hydrothermal,⁵ and electrochemical deposition,⁶ as well as physical⁷ and chemical^{8,9} vapour deposition techniques. It is worth mentioning that the use of chemical vapour deposition methods to synthesise TiO₂ materials presents advantages over other methodologies, such as removing the need for a calcination/annealing step which can drastically affect the nature and content of the dopant,¹⁰ and ease of industrial scale up.

TiO₂, however, presents some disadvantages such as low conductivity and poor electron mobility which limits its usage for optoelectronic devices such as transparent conductive oxides (TCO).^{11,12} Even when donor doped with Nb or W, resistivities fail to reach those of doped SnO₂, In₂O₃, ZnO or BaSnO₃. Anatase TiO₂ possesses a wide band gap (E_g ~3.2 eV) making it a UV absorber, limiting its efficiency as a photocatalytic material. To improve upon this and modify the morphology of TiO₂, acceptor doping with a non-metal or a transition-metal, has become one of the most widely studied areas of research in photocatalysis and materials science.¹³

Generally, upon acceptor doping, such as with nitrogen, the N 2p states sit slightly higher than the O 2p states at the valence band maximum (VBM) reducing the band gap and improving the efficiency of visible light absorption. However when donor doped, the conductivity increases but usually at the expense of the photocatalytic activity. The majority of research on this has been in acceptor doping with non-metals such as N, C or B.¹⁴

Boron doping of TiO₂ has attracted attention due to its enhanced photocatalytic activity under visible light.¹⁵

When boron is doped into the TiO₂ lattice it can occupy both substitutional oxygen and titanium sites (B_O and B_{Ti} respectively) as well as interstitially (B_i) making it an *amphoteric* dopant. Experimentally a blue shift is observed in the band edge of TiO₂:B when boron occupies an interstitial site indicative of a Moss-Burstein shift.¹⁶ In addition, studies showing a red shift in the absorption edge are suggestive of substitutional B. This has been postulated as the creation of mid-gap states acting as absorption centres enhancing the visible light absorption and photocatalytic activity.¹⁷ It has been suggested in the literature that interstitial boron reduces Ti⁴⁺ to Ti³⁺ promoting the separation of the photoexcited electron and hole pairs suppressing their recombination and enhancing the photocatalytic activity.¹⁶ It should be noted, however, that excess electrons in anatase TiO₂ are generally delocalized in the bulk, but can localize on the surface.¹²

Previous synthesis of TiO₂:B has been focused on the formation of powders by sol-gel, annealing and hydrothermal methods.¹⁵ Recently, TiO₂:B thin films deposited by APCVD were reported for the first time by Carmichael *et al.*¹⁸ Analysis of the films showed substitutional boron which lead to remarkable rates of hydrogen production (24 μL cm⁻² h⁻¹) and more favourable photocurrent profiles when compared to un-doped samples. Other APCVD routes have created interstitial B-doped TiO₂ with the noticeable effect of interstitial boron in the surface morphology of the thin films.¹⁹ The films showed higher rates of photoactivity together with higher stability when compared to substitutional boron-doped TiO₂ films. Here, we present and report the study of the synthesis and characterisation of a series of interstitial TiO₂:B thin films, synthesised by one-step APCVD, containing different concentrations of boron. The impact which interstitial boron has on the morphology, structure and functional properties of such films is shown experimentally and by state-of-the-art *ab-initio* theoretical methods.

2. Experimental Methodology

The chemicals were purchased from Sigma-Aldrich and Acros Organics. Titanium tetrachloride (TiCl₄, 99.9%), ethyl acetate (C₄H₈O₂, 99.8%), and triisopropyl borate (C₉H₂₁BO₃, 98%) were used as titanium, oxygen, and boron sources, respectively. Octadecanoic (stearic) acid (CH₃(CH₂)₁₆CHO₂, 98.5%) was used to perform the photocatalytic assay.

2.1 Atmospheric Pressure Chemical Vapour Deposition (APCVD)

The boron-doped TiO₂ thin films were synthesised in a custom-built cold-walled CVD reactor at atmospheric pressure.²⁰ The reactor consisted of a graphite block (320 mm-long × 150 mm-width) contained within a quartz glass tube. The graphite block contained three embedded Whatman heater cartridges and the temperature was controlled using Pt–Rh thermocouples. Nitrogen gas (supplied by BOC) was used as the carrier gas to lead the precursor vapours into the reactor. The gas mixture was introduced through a triple manifold in order to ensure a laminar flow into the reactor. The carrier gas was pre-heated at 473 K and all the pipes of the CVD system were kept at that tem-

perature. The precursors were heated independently in stainless steel bubblers in order to maintain their intended vapour pressures and ensure flow rate control. Before entering the CVD reactor, the precursors were quickly mixed in stainless steel mixing chambers at 523 K, under controlled flow rate conditions.

The films were deposited at 773 K on float glass substrates (89 × 225 × 4 mm) supplied by the Pilkington NSG Group, pre-coated with a SiO₂ barrier layer to prevent ion diffusion from the glass into the film. The glass substrates were cleaned using distilled water, acetone (99%) and isopropanol (99.9%) and dried in air prior to use. In a typical deposition, the temperature and mass flow rates were constant for metal (TiCl₄) and oxygen (CH₃COOC₂H₅) precursors as 340 and 310 K and 6.4 × 10⁻³ and 3.04 × 10⁻³ g·min⁻¹, respectively. A range of boron-doped TiO₂ films (TiO₂:B) were synthesised using increasing mass flow rates of triisopropyl borate (C₉H₂₁BO₃) as boron precursor, namely 0.19 × 10⁻³ g·min⁻¹ (sample A) 0.56 × 10⁻³ g·min⁻¹ (sample B) and 0.65 × 10⁻³ g·min⁻¹ (sample C).

2.2 Analytical Methods

X-ray diffraction (XRD) patterns of the films were obtained using a Lynxeye XE Bruker-Axs D8 diffractometer. The instrument operates with a Cu X-ray source, monochromated (Kα₁, 1.5406 Å). Films were analysed with a glancing incident angle (θ) of 1°. Structural analysis of the powdery deposition was done by Powder XRD using a Bruker D4 Bragg–Brentano theta-2 theta reflection geometry machine equipped with Cu Kα₁₊₂ source powered at 40 kV, 30 mA coupled with a post-sample graphite monochromator and scintillation counter detector. The Joint Committee on Powder Diffraction Standards (JCPDS) was used to determine the crystal structure adopted. The lattice parameters and average crystal size was determined using a Le Bail model using the GSAS-EXPGUI software suite.²¹ Raman spectroscopy was carried out using a Renishaw 1000 spectrometer equipped with a 514-nm laser. The Raman system was calibrated using a silicon reference.

Characterisation of the chemical profile of the thin films was carried out by Dynamic Secondary Ion Mass Spectrometry (D-SIMS) in a Cameca SC-Ultra instrument in positive ion mode, by a bombardment with Cs⁺ ions, having an impact energy of 1.0 keV.

X-ray photoelectron spectroscopy (XPS) was used to determine the composition of the films and spectra were recorded on a Kratos Axis Nova spectrometer equipped with a monochromated Al Kα X-ray source and delay line detector. Survey spectra were recorded with energy of 160 eV and higher resolution spectra were recorded at 80 eV. A Filmetrics F20 single spot thin film machine was used to analyse film thicknesses. UV/visible spectroscopy was performed using a double monochromated PerkinElmer Lambda 950 UV/vis/NIR spectrophotometer in the 300–2500 nm range. Reflectance spectra were recorded for different positions in the range 300–2500 nm on a Helios double beam instrument standardised relative to a silicon mirror, which allowed the thickness of the films to be also be determined via the Swanepoel method.²² The morphology of the films was studied by Scanning Electron

Microscopy (SEM). The images were taken using JEOL 6301 (5 kV) and a JEOL JSM-6700F field.

The probe measurements (Hall Effect) were conducted at room temperature on an Ecopia HMS-3000 device in the Van der Pauw configuration²⁷. Measurements were acquired at 0.58 T and a variable current of 0.1 μA to 1 nA on square-cut samples ($\approx 1 \times 1 \text{ cm}$). Silver paint (Agar Scientific) was used to form ohmic contacts, the integrity of which were tested prior to measurement.

2.3 Photocatalytic Test

The photocatalytic activity of the films was evaluated during photodegradation of octadecanoic (stearic) acid. A thin layer of stearic acid was applied on the surface of the samples by dip-coating from a stearic acid solution (0.05 M) in chloroform under UVA illumination (BLB Vilber-Lourmat, $2 \times 8 \text{ W}$, 365 nm, 2 mW cm^{-2}). A PerkinElmer RX-I Fourier transform infrared (FTIR) spectrometer was used to monitor the disappearance of characteristic C–H modes of the acid (2958 cm^{-1} , 2923 cm^{-1} , and 2853 cm^{-1}). The photocatalytic rates were estimated from linear regression of the initial steps (30–40%) of the curve of the integrated area vs illumination time. This estimation considered that $1 \text{ cm}^{-1} \equiv 9.7 \times 10^{15} \text{ molecules}^{23}$

3. Theoretical Methodology

Computational analysis using *ab-initio* methods has been carried out on the intrinsic defects and boron incorporation in anatase TiO_2 . These calculations have been carried out using the Vienna *Ab-initio* Simulation Package, VASP^{24–27}, a periodic boundary, plane-wave density functional theory (DFT) code. The projector-augmented wave method (PAW)²⁸ was employed to describe the interactions between the core electrons and the valence electrons of each species (Ti:[Ar], O:[He] and B:[He]).

In this study the *hybrid* DFT functional, HSE06 (Heyd-Scuzeria-Ernzerhof)^{29,30} was used to obtain accurate electronic and geometric results of B-doped TiO_2 . Hybrid functionals are less inhibited by the short falls of standard DFT functionals which fail to describe the *self-interaction* error and thus underestimate band gaps resulting in an inaccurate picture of the defect chemistry of a system. Hybrid functionals have consistently displayed increased accuracy over standard DFT functionals in describing both the geometry and electronic structure for a range of semiconductors and insulators,^{12,31–41} and HSE06 has been shown to provide a good description of all polymorphs of TiO_2 .^{12,42–48}

A geometry optimization was carried out on the primitive cell of anatase TiO_2 allowing the lattice vectors and angles, volume, and atoms to relax until the forces on all the atoms were less than $0.01 \text{ eV atom}^{-1}$. In order to achieve an accurate convergence of the total energy and electronic structure, a 700 eV plane wave energy cutoff and a Γ -centred $7 \times 7 \times 5$ k-point lattice were used.

All the defect states calculated herein were simulated using a $3 \times 3 \times 1$ supercell containing 108 atoms using a Γ -centred k-point mesh of $2 \times 2 \times 2$ combined with a plane

wave cutoff of 450 eV. Only the ions within the supercells were allowed to relax with the lattice vectors and angles kept fixed. All the defect calculations were spin-polarised, and the systems were deemed to be converged when the forces on all the atoms were less than $0.01 \text{ eV atom}^{-1}$. The limiting phases were calculated using plane-wave energy cutoffs of 700 eV and Γ -centred k-point meshes of $6 \times 6 \times 3$ and $8 \times 8 \times 8$ for B_2O_3 and Ti_2O_3 respectively.

3.1 Defect Formalism

The formation energy of a defect in charge state ‘q’ is defined as:

$$\Delta H_f(\text{D}, q) = (E^{\text{D},q} - E^{\text{H}}) \pm \sum_i n_i E_i(E_i + \mu_i) + q(E_{\text{Fermi}} + \varepsilon_{\text{VBM}}^{\text{H}} + \Delta E_{\text{pot}}) + q^2 E_{\text{corr}}^{\text{IC}} + E_{\text{corr}}^{\text{BF}} \quad (1)$$

$E^{\text{D},q}$ and E^{H} refer to total energies of the defective cell in charge state ‘q’ and the host cell respectively. E_i refers to the elemental reference energy (where ‘i’ is $\text{Ti}_{(\text{s})}$, $\text{O}_{2(\text{g})}$ or $\text{B}_{(\text{s})}$) and μ_i is the associated chemical potential. n refers to the number of electrons taken away from or added to the external reservoir. In this work the Fermi level (E_{Fermi}) ranges from the valence band maximum (VBM) (0 eV) to $\sim 1.7 \text{ eV}$ above the conduction band minimum (CBM). $\varepsilon_{\text{VBM}}^{\text{H}}$ refers to the eigenvalue of the VBM in the host material and ΔE_{pot} corresponds to the correction that is applied to account for the difference between the potential of the host and the defective supercells. Two more corrections are applied to account for the finite size effects of the supercell; the first is an *image charge correction* $E_{\text{corr}}^{\text{IC}}$ which corrects for the interaction of the charged defect and its own periodic images due to the long ranged nature of the Coulomb interaction.^{49,50} The *image charge correction* implemented herein uses the scheme formalised by Hine and Murphy⁵¹ which utilises the dielectric tensor. Lastly there is a *band filling* correction ($E_{\text{corr}}^{\text{BF}}$) by Lany and Zunger^{52,53} which is applied to shallow defects to account for the high defect concentrations present in supercell calculations.

3.2 Chemical Potential Limits

The chemical potentials in **Equation (1)** (μ_i) can reflect the equilibrium growth conditions which can then be varied to simulate the experimental partial pressures defining the extremes of *n*-type and *p*-type defect formation. Under equilibrium conditions the chemical potentials are relative to the formation enthalpy of anatase:

$$\mu_{\text{Ti}} + 2\mu_{\text{O}} = \Delta H_f^{\text{TiO}_2} = -9.14 \text{ eV} \quad (2)$$

Due to the requirement that TiO_2 is to be thermodynamically stable towards Ti_2O_3 , a further restraint is imposed on the chemical potentials making the *Ti-rich/O-poor* boundary limited by:

$$2\mu_{\text{Ti}} + 3\mu_{\text{O}} = \Delta H_f^{\text{Ti}_2\text{O}_3} = -14.76 \text{ eV} \quad (3)$$

These results correlate well with room-temperature experimental values (-9.73 eV and -15.76 eV for TiO₂ and Ti₂O₃ respectively⁵⁴).

This results in the ‘extreme’ set of growth conditions:

Ti-rich/O-poor (*n*-type favourable) where the chemical potentials are limited by the formation of Ti₂O₃:

$$\mu_{\text{Ti}} = -2.11 \text{ eV}; \mu_{\text{O}} = -3.51 \text{ eV} \quad (4)$$

And for *Ti-poor/O-rich* (*p*-type favourable) conditions where the chemical potentials are limited by the formation of O_{2(g)}:

$$\mu_{\text{Ti}} = -9.14 \text{ eV}; \mu_{\text{O}} = 0 \text{ eV} \quad (5)$$

To determine the solubility of the boron species, a limitation via the formation of a secondary phase, B₂O₃ is applied and is calculated to be:

$$2\mu_{\text{B}} + 3\mu_{\text{O}} = \Delta H_f^{\text{B}_2\text{O}_3} = -13.09 \text{ eV} \quad (6)$$

(The experimental formation energy at room temperature is determined to be -13.20 eV⁵⁴)

Therefore, under *Ti-poor/O-rich* and *Ti-rich/O-poor* conditions $\mu_{\text{B}} = -6.55 \text{ eV}$; $\mu_{\text{B}} = -1.27 \text{ eV}$ respectively

The thermodynamic transition levels are displayed below (**Figure 8**) and show the evolution of a defect from charge state *q* to *q'* at a certain Fermi level position calculated by:

$$\epsilon_{\text{D}} \frac{q}{q'} = \frac{\Delta H_f(\text{D},q) - \Delta H_f(\text{D},q')}{q' - q} \quad (7)$$

Experimentally these transition levels can be seen by such techniques as deep level transient spectroscopy (DLTS).

4. Results and discussion

A series of B-doped TiO₂ thin films, henceforth samples *A*, *B* and *C*, were produced by APCVD containing various boron concentrations, as indicated in Table 1. The concentration of boron in the films were increased by varying the temperature of the bubbler and the mass flow rate. All the films were strongly adherent and passed the Scotch™ tape test, except for those using high flow rates of the boron precursor (*e.g.* sample *C*), which showed powdery areas across the glass substrate (Figure S2). The powder was easily removed using water or acetone. The formation of this powdery areas will be discussed below (*vide infra*).

4.1 Boron doping

The presence of boron in the films and its oxidation state was elucidated using XPS and D-SIMS (Figure 1 and Figure S2). The Ti *2p* peaks, located at binding energies of 458.9 eV and 464.6 eV were identified as Ti-O bonds of Ti⁴⁺ in TiO₂ (Figure S3a).²⁰ No other Ti⁴⁺ environment or reduced Ti³⁺ species were detected.

The O *1s* peak, located at 530.4 eV, is also consistent with the formation of TiO₂. The total boron concentration of the TiO₂:B films was found to be in the range of 1-5 at.% (table 1). Many discrepancies can be found in the literature with regards of the chemical environment of boron in boron-doped TiO₂ materials. Generally, B *1s* peaks at 190–191 eV are attributed to substitutional boron in an oxygen position (B_o) and peaks in the range 191–192 eV correspond to interstitial boron (B_i).⁵⁵ Boron can also be found in various

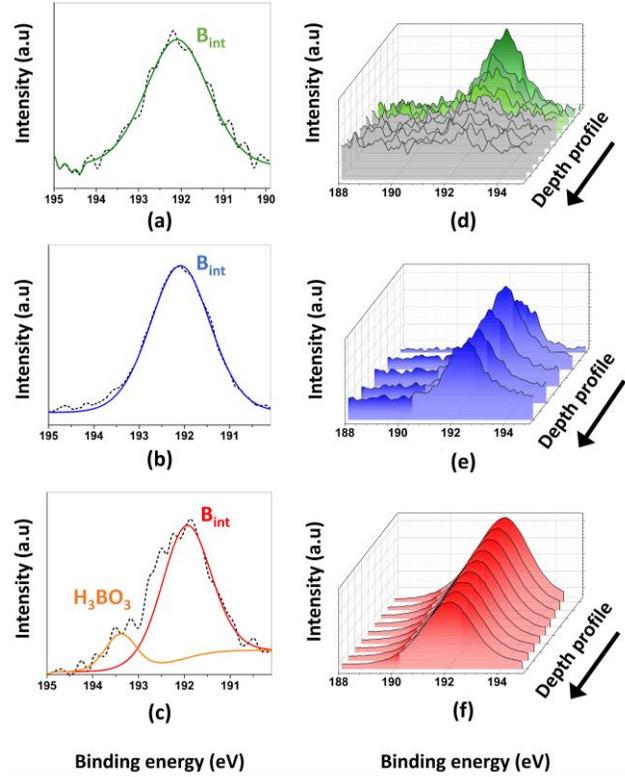


Figure 1. B *1s* XPS surface and in depth profile spectra of TiO₂:B samples: (a) TiO₂:B (A); (b) TiO₂:B (B) and (c) TiO₂:B (C); (d, e and f) depth profiling spectrum of TiO₂:B (A), TiO₂:B (B), TiO₂:B (C) thin films, respectively. Dashed black lines in figures a, b and c represent the raw data (CPS) in XPS.

other forms, including cationic B³⁺ in B₂O₃ and anionic B²⁻ in TiB₂, with characteristic B *1s* peaks at 193.1 eV and 187.5 eV, respectively.^{15,55} Our XPS results confirmed the presence of interstitial B_i alone in most samples, with peaks within the range of 191.5–192 eV in the B *1s* environment. High flow rates of the boron precursor induced formation of boric acid, as identified by an additional peak at 193.5 eV (Figure 1c).¹⁹ This peak, however, was only observed from surface analysis in sample C, not in the bulk of the sample (Figure 1f). The concentrations of boron in the bulk of the samples ranged between 0.8–1, 2–3 and 4–5 at. % for samples *A*, *B* and *C*, as indicated in Table 1. Further analysis was carried out using D-SIMS (Figure S3b, c and d). It could be seen that, while the content of titanium and oxygen remained constant, the content of boron varied within the bulk of the films. In the case of samples *A* and *B*, boron is found mostly through the bulk of the film, as seen by D-SIMS depth profiling (Figure S3b and c), whereas, in the case of sample *C*, boron is found mostly on the surface of the thin film through at least ~10 nm, as XPS depth profiling analysis revealed (Figure 1f).

4.2 Structure discussion

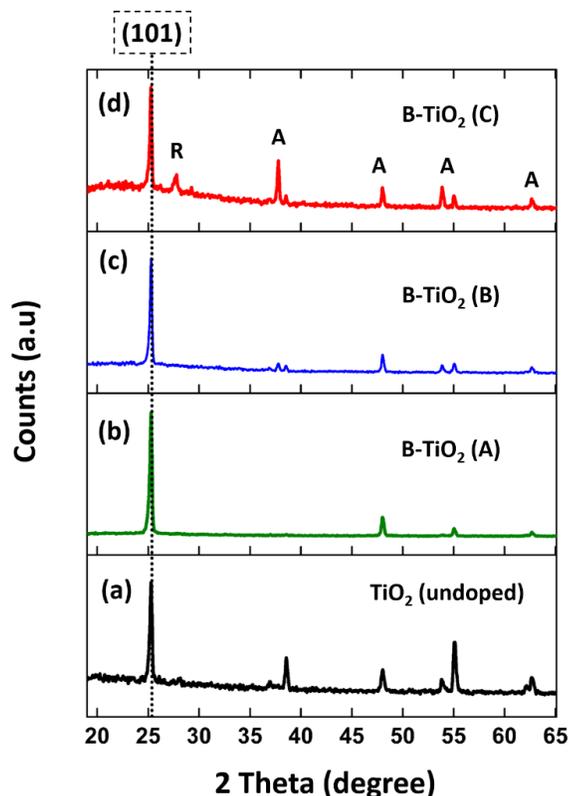


Figure 2. XRD patterns of undoped and B-doped TiO₂ thin films (A = anatase and R = rutile); (a) undoped TiO₂; (b) sample TiO₂:B (A); (c) sample TiO₂:B (B); (d) sample TiO₂:B (C). Dotted line represents the crystalline plane (101) of anatase.


X-ray diffraction (XRD) and Raman spectroscopy were used to study the crystal structure of TiO₂ present in the TiO₂:B thin films. **Figure 2** shows XRD patterns of TiO₂:B samples alongside an undoped TiO₂ thin film. The lattice parameters were determined using a Le Bail model, tooled with GSAS and compared with literature powder standards of anatase and rutile TiO₂.⁵⁶ All samples confirmed the presence of anatase TiO₂ only, except for sample C that showed traces of the rutile phase, as evidenced by an additional peak at $2\theta = 27.7^\circ$ (Figure 2d). The proportion of rutile phase in sample C, calculated from the XRD data, was estimated around a relative value of ~15% of the total. The presence of rutile at relatively low temperature –the typical anatase-rutile transformation temperature is above 700 °C– can be explained from changes in the pH of the precursors mixture in the gas phase, which may induce changes in the nucleation rates of the TiO₂ nanoparticles. As previously reported by Sabyrov *et al.*,⁵⁷ the generation of smaller initial nanoparticles of anatase TiO₂ in acidic

conditions and at high temperatures increased and induced the phase transformation rate of rutile TiO₂. Pore *et al.*⁵⁸ reported a similar effect for the synthesis of S-doped TiO₂ films using atomic layer deposition (ALD).


Extracted from Le Bail refinement, the average crystallite size of the doped samples increased compared to undoped TiO₂ (Table 1) but decreased upon apparently increasing levels of boron in the structure. A potential explanation for this is a concurrent formation of a boron-containing by-product upon increasing flow rates of the boron precursor. This is plausible considering that the B 1s XPS peaks in the bulk were weak and broad (Figure 1d, 1e and 1f) and thus the levels of doped boron in the TiO₂ structure may be overestimated. The mentioned by-product could be boric acid (H₃BO₃), as inferred from the XPS results from sample C (Figure 1c). The formation of boric acid (or sassolite) was indeed confirmed by XRD analysis of the powdery sections in this sample (Figure S2).

XRD also suggested the addition of the boron dopant in an interstitial position. Indeed, the lattice parameter *c* (Table 1) of TiO₂:B, were shown to be larger than the ones of the reference TiO₂ sample.

The unit cell volume in sample B is similar to the undoped TiO₂ film synthesised under the same conditions. The extension of the *c*-axis and the expansion of the unit cell volume can be explained by the interstitial incorporation of boron in the TiO₂ lattice.^{17, 19} Raman spectroscopy studies of the as-synthesised samples (Figure 3a) confirmed the presence of anatase TiO₂ in the samples, following the characteristic bands at 144, 400, 650 cm⁻¹.⁵⁶ Doped TiO₂ anatase samples are often characterised by a shift of the E_g mode at 144 cm⁻¹.^{59,60} Close inspection of Figure 3b, however, only showed a blue shift of the E_g mode for sample A, allegedly the sample with the lowest boron content (Table 1). This observation seems to support our previous comments with regards of the actual B content in the samples, based on XPS and XRD results (*vide supra*). The suggested mechanism of formation of TiO₂ from reaction between TiCl₄ and ethyl acetate has been described according to the following equations:⁶¹



These involve the decomposition of ethyl acetate to produce oxidising species such as ethanol (Eq. 1a), which in turn dehydrates into water and ethane (Eq. 1b). With water present, the surface reaction may proceed by hydrolysis of TiCl₄ according to Eq. 1c. In the presence of triisopropyl borate, however, reaction with water may lead to boric acid following Eq. 2.



Sample	phase	a [Å]	b [Å]	c [Å]	V [Å ³]	τ (nm)	[B] (at. %)
Standards	anatase	3.7848(3)	3.7848(3)	9.5124(2)	136.26	-	N/A
	rutile	4.5941(1)	4.5941(1)	2.9589(1)	62.45	-	N/A
Undoped	anatase	3.7885(4)	3.7885(4)	9.5205(4)	136.13	44.63	0
TiO₂:B (A)	anatase	3.7832(1)	3.7832(1)	9.5322(7)	137.65	87.43	0.8-1.0
TiO₂:B (B)	anatase	3.7811(8)	3.7811(8)	9.5087(2)	135.94	79.51	2.0-3.0
TiO₂:B (C)	anatase	3.8003(4)	3.8003(4)	9.5361(6)	137.72	50.26	4.0-5.0
	rutile	4.5298(9)	4.5298(9)	2.9598(5)	60.73	31.21	4.0-5.0

Table 1. Cell parameters, unit cell volume (V), crystallite size (τ) and boron content (in at. %) of the undoped and TiO₂:B thin films. Error: Volume (Å³) ± 0.1%; Crystal size (τ, nm) ± 1%.

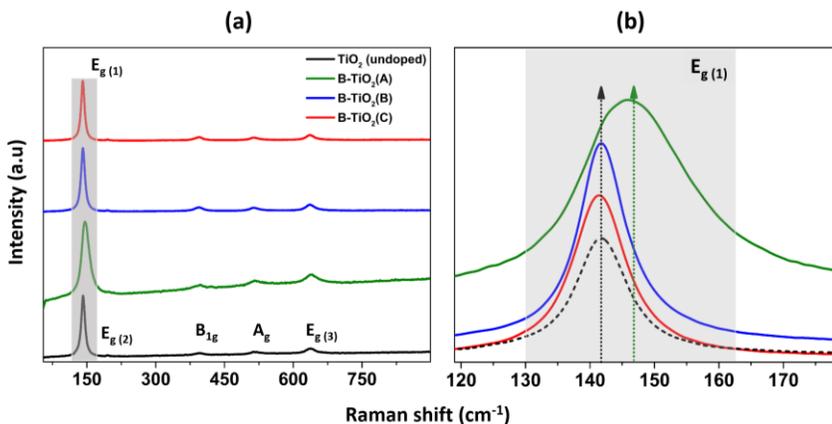


Figure 3. (a) Raman spectra of the TiO₂:B samples, compared to the undoped anatase film and (b) Raman shift of the Eg band zoomed. Black dotted arrow (left) indicates the position of the undoped TiO₂ and dotted green arrow (right) the position of the Eg(1) band for TiO₂: (A).

4.3 Morphology of the TiO₂:B films

The mass flow rate of the boron precursor had a drastic impact on the morphology of the films. A typical SEM image of the undoped TiO₂ film showed shell-shaped aggregated particles with sizes in the range of 120 - 230 nm (Figure 4a), which contrasted with the significantly large average particle size of the TiO₂:B samples. In Figure 4b, sample A showed agglomerations of big particles (ca. 1 μm to 2.3 μm) with a more defined prism-like and cubic shape deposited on top of a uniform coating of smaller agglomerations of particles. Both type of deposited particles were well adherent to the substrate forming a bilayer-like structure of TiO₂:B as reported previously.¹⁹ In contrast, sample B, exhibited a well-defined and uniform film composed of cubic-shaped particles (ca. 160 nm). Sample C (Figure 4d) showed prism-shaped and well aggregated particles with sizes in the range of 300 nm to 500 nm. Comparing the different surface morphologies of TiO₂:B (Figure 4b, c and d) with the undoped TiO₂ film (Figure 4a), the final concentration of boron incorporation has a significant role in the agglomeration of the doped-TiO₂ particles along the substrate. The SEM cross-section images of the samples (Figure 4e, 4f, 4g and 4h) show that both the undoped and doped TiO₂ thin films described in this work were relative-

ly hard and strongly adhered along the entirety of the glass substrate. In the case of sample A, the cross-section SEM analysis (Figure 4f) confirmed what can be seen in the top view image (Figure 4b), the multilayer-like morphology, where agglomerations of larger particles of TiO₂:B (cubic shape) can be found on top of a uniform layer of smaller particles. The thicknesses of the films were found to be in the range between 420 nm to 650 nm.¹⁹

As it can be seen in Figure 4, the different TiO₂:B films deposited showed varying morphology, associated with the boron doping level. SEM observations supported the existence of morphology discrepancies between the TiO₂:B samples (Figure 4b, c and d) and the undoped TiO₂ coatings (Figure 4a). In addition, SEM analysis of the TiO₂:B samples revealed the presence of 3 different morphologies which correspond to the macroscopic aspect variation observed on the substrate (Figure S1), i.e., visual observations under tilt angle of sample A presented areas containing concentric circles whereas sample B and C showed different lines of interference colours, expressing thickness differences along the length of the substrate.¹⁹

4.5 Optical properties of the films

The undoped TiO₂ thin films displayed high optical transparency. The incorporation of low B concentrations (sample A, ~1 at.%) resulted in films with zones of concentric circles on the substrate evidenced by a red shift in the transmission onset from 316 nm to 348 nm compared to the undoped TiO₂ thin films (**Figure 5a**). Surprisingly, the

shift was not so drastic for the highly doped films (samples B and C). These results are similar to phosphorous doped TiO₂ thin films by C. Sotelo-Vazquez *et al.*⁶⁰, where it was reported a small shift (blue shift in their case) when the concentration of the dopant (phosphorus) was lower than 1 at. %, and no noticeable shift occurs when the concentration was higher than 1 at. %.

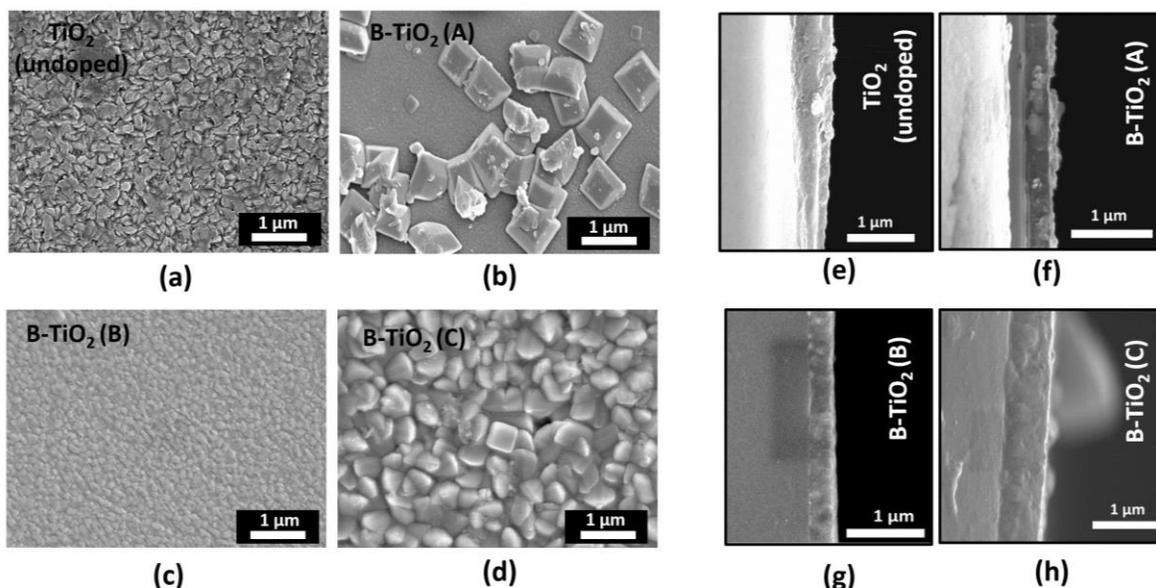


Figure 4. SEM images (top view) of: (a) Undoped TiO₂, (b) TiO₂:B (A), (c) TiO₂:B (B) and (d) TiO₂:B (C); Cross-section SEM images (e, f, g and h) of the undoped and boron-doped thin films, respectively.

Tauc plot analysis (**Figure 5b**) showed a slight shift in absorption into the blue region for the doped TiO₂ samples compared to the *experimental* value for undoped films (~3.45 eV), with band gap energies estimated around 3.28, 3.36 and 3.43 eV for samples A, B and C, respectively. Valence band XPS (VB-XPS) shows the valence band edge relative to the Fermi level for the undoped and boron-doped TiO₂ samples (**Figure S6**), corroborating the band gap shifts.

4.5 Functional properties of the TiO₂:B films

The photocatalytic properties of the TiO₂:B films were investigated during degradation of stearic acid under UVA and visible light irradiation.²³ **Figure 6a** shows the corresponding photocatalytic activities under UVA light (2 mW·cm⁻²), expressed in terms of formal quantum efficiency (FQE), which is defined as molecules of stearic acid degraded over incident photons (molecule/photon). All the TiO₂:B samples showed improved photocatalytic activities compared to a conventional undoped anatase TiO₂ film. This is not surprising considering that the incorporation of interstitial boron encouraged crystallinity (**Figure 2**) and increased crystallite size (**Table 1**). This is certainly the case for the incorporation of relatively low levels of boron in the structure (~1 at.%) as observed for sample A. The synthesis conditions in the presence of higher concentrations of boron precursor induced lower crystallite sizes for

samples B and C, respectively, and the photocatalytic activities were observed to follow the same trend (**Figure 6b**). Nevertheless, as seen in the XRD patterns (**Figure 2d**) the boron-doped TiO₂ sample C contains simultaneously rutile and anatase. The presence of rutile has been also reported to have a direct impact in the photocatalytic performance of TiO₂. Reported by D. O. Scanlon *et al.*⁴⁴ photogenerated conduction electrons will flow from rutile to anatase, inducing a type II band alignment (~0.4 eV), significantly reducing the effective bandgap of composite materials, and improving efficient electron–hole separation. This alignment increased the photoactivity of anatase–rutile composite materials over their individual analogues.

The conductivity of the doped films was also investigated using a Hall Effect probe and the results are summarised in **Table 2**. As the resistivity was close to the detection limits of the Hall Effect device, the derived charge carrier densities and mobilities were liable to have large associated errors. A high resistivity and small range of mobility of the charge carriers was measured. It was found that the lowest resistivity was found for sample B (20 Ω cm) whilst the highest was for Sample C (9.5 × 10⁵ Ω cm). Comparing these values to Nb:TiO₂ and F:TiO₂, the measured values of resistance (**ρ**) for TiO₂:B are much higher.

4.5 Bulk electronic properties:

The density of states (DoS) and band structure for anatase TiO₂ are presented in **Figure 7a and b** respectively. The DoS shows that the VBM is predominantly made up of O 2p states mixed with some negligible Ti p and d states. On the other hand, the CBM is mostly made up of Ti d states alongside a minimal amount of O states. These results are consistent with other DFT calculations on TiO₂ polymorphs.^{44,62} **Figure 7b** shows that anatase is an indirect band gap material ($E_g^{\text{ind}} = 3.35$ eV) with the VBM occurring just off the Z high symmetry point (between Γ and Z) and

the CBM at Γ . The direct band gap at Γ has a magnitude of 3.64 eV. These results are consistent with other theoretical calculations using HSE06^{63,64} and low temperature optical studies (3.42 eV),⁶⁵ however the general consensus in experiment places the band gap at ~ 3.2 eV.⁴⁴ Higher levels of theory such as the GW (Green's function) approximation which place the band gap around 3.6-3.8 eV,⁶⁶⁻⁶⁹ the over-estimation is generally thought to be excitonic effects or the difficulties in the convergence of the screened interaction of localized systems.⁶⁷⁻⁶⁹

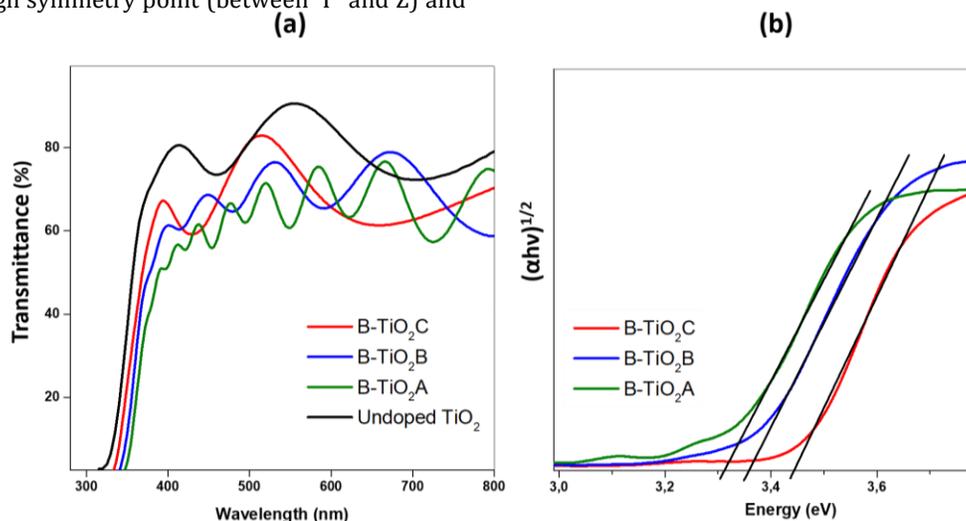


Figure 5. (a) UV-visible spectra (transmittance) of the doped and undoped TiO₂ films, (b) graphical calculation (Tauc plot) of the optical band gap for all the boron-doped TiO₂ samples.

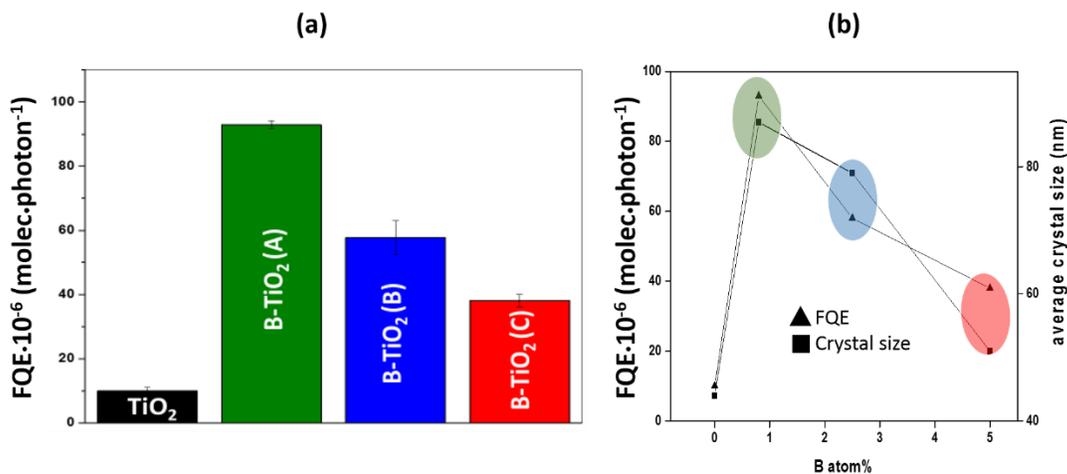


Figure 6. (a) Formal quantum efficiencies (FQE) obtained during photodegradation of stearic acid under UVA irradiation of undoped and boron-doped TiO₂ films (**Table 1**); (b) comparison between photocatalytic activities and crystallite sizes as determined from XRD analysis. Crystal size data presented in table 1.

	Hall effect probe			Resistance	
	Sample	n (cm ⁻³)	μ (cm ² V ⁻¹ s ⁻¹)	ρ (Ω cm)	R (K Ω)
Ta-extracted Effect Electri- ments. (*)	TiO ₂ :B (A)	-3.24×10^{15}	172.40	112	150 \pm 3
	TiO ₂ :B (B)	-3.82×10^{17}	8.17	20	90 \pm 1
	TiO ₂ :B (C)	-9.00×10^{13}	0.08	9.5×10^5	120 \pm 5
	Nb:TiO ₂ (*)	-8.30×10^{18}	3.4	0.22	--
	F:TiO ₂ (*)	-46.00	26	5.2	--

ble 2. Data from the Hall cal Measure- From ref: 35.

4.6 Defect Thermodynamics:

Figure 8 shows the transition level diagrams for TiO₂:B under both *Ti-rich/O-poor* and *Ti-poor/O-rich* conditions.

4.6.1 Intrinsic defects:

Previous theoretical studies have shown that the dominant acceptor and donor defects in anatase are the titanium vacancy (V_{Ti}) and the oxygen vacancy (V_O).^{46,48,70-73} Under *Ti-rich/O-poor* conditions, V_O acts as a *resonant donor* with a low formation energy (for V_O^0 , $\Delta H_f = \sim 1.19$ eV) with the 2+

charge state dominant across the entirety of the band gap. This is in contrast to most wide band gap binary oxides such as ZnO^{34,74-76}, SnO₂⁷⁶⁻⁷⁹, In₂O₃^{42,76,80-83} and BaSnO₃⁸⁴ where V_O is a “negative-U” defect modulating from the 2+ to the neutral charge state in the band gap. Under *Ti-poor/O-rich* conditions, V_O has a higher formation energy ($\Delta H_f = \sim 4.71$ eV). These results are consistent with other theoretical studies carried out on anatase.^{48,70,85,86}

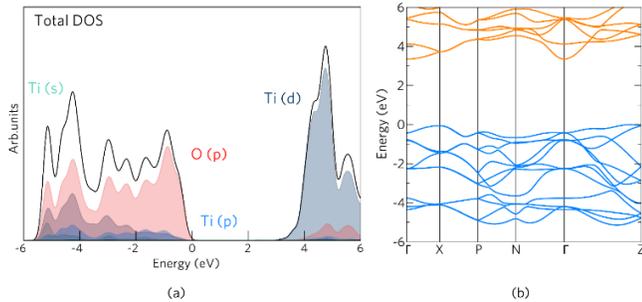


Figure 7. The calculated density of states (DoS) (a) and band structure (b) of undoped anatase TiO₂. In each diagram the valence band maximum (VBM) is set to 0 eV. In (b) the valence bands are depicted as blue lines and the conduction bands as orange lines.

V_{Ti} is a *deep* acceptor under both growth regimes with the 1-/0 transition level occurring at ~ 0.87 eV above the VBM. The formation energies of the neutral charge state occur at ~ 14.26 eV and ~ 7.23 eV for *Ti-rich/O-poor* and *Ti-poor/O-rich* conditions respectively, meaning that the formation of V_{Ti} near the VBM is highly unfavourable and will be seen in negligible quantities. Under *Ti-poor/O-rich* conditions (*p*-type favourable), V_{Ti}^{4-} begins compensating the donor defects ~ 2.28 eV above the VBM. Our calculations show that

all charge states of V_{Ti} are shown in the band gap. Multiple pictures of V_{Ti} are seen in the theoretical literature on anatase. Phattalung *et al.*⁸⁷ found using LDA (Local Density Approximation) that V_{Ti} is a quadruple *shallow* acceptor, however LDA is known to be inadequate in describing the band gap and correct localization of holes and electrons. Applying a Hubbard-like “U” value (which incorporates an occupation penalty scheme), Morgan *et al.* show that V_{Ti} is a *deep* acceptor (2-/0 transition occurs ~ 0.85 eV above the VBM). In this study, however, it is shown that there is no 0/1- transition level and the formation energy is ~ 2.5 eV lower than that calculated from our calculations.^{70,73} The only HSE06 calculations on V_{Ti} in anatase show that the defect transitions from the neutral charge state to the 2- then the 4- charge state over the band gap. In these calculations only a Monkhorst-Pack 1x1x1 k-point sampling was used which can lead to inaccurate total energies and therefore uncertainty in the thermodynamic picture of the defects.⁴⁸

It is known that the thermodynamic transition levels can be sensitive to the correct localization and delocalization of electrons and holes and **Figure 9** presents the calculated partial charge densities of each charge state of V_{Ti} displaying the correct localization of holes on the adjacent oxygens surrounding the vacancy. The axial holes are the first to be removed (V_{Ti}^{1-} and V_{Ti}^{2-} which are depicted as p_y orbitals) and then the equatorial holes (V_{Ti}^{3-} and V_{Ti}^{4-} depicted as p_z orbitals). This correct localization is important and we have shown this to be as important in ZnO.⁸⁸

4.6.2 B-Doping:

Boron can enter the anatase lattice interstitially (B_i) or substitutionally on a titanium site (B_{Ti}) or oxygen site (B_O). Previous theoretical studies have been carried out on TiO₂:B^{16,89-93} in particular, a study by E. Finazzi and coworkers¹⁸ which gives a fairly comprehensive view on the electronic structure of various B related defects.

Under *Ti-rich/O-poor* conditions, B_i^{3+} is lowest in energy across the whole band gap, meaning that interstitial boron is the most preferential dopant state to form. B_i acts as a shallow dopant donating 3 electrons into the conduction band and has a very low formation energy. The Fermi level is pinned in the conduction band at ~ 0.65 eV above the CBM when the V_{Ti}^{4-} charge state falls low enough in formation energy to begin compensation of the donated elec-

trons. Under *Ti-poor/O-rich* conditions, the formation energy of B_i is raised in energy and the Fermi level is pinned in the band gap ~ 2 eV above the VBM when B_{Ti}^{1-} and V_{Ti}^{4-} cross those of B_i^{3+} and V_o^{2+} . In **Figure 10a, 10b and 10c**

the partial charge localization is shown for B_i in the 0, 1+ and 2+ charge states.

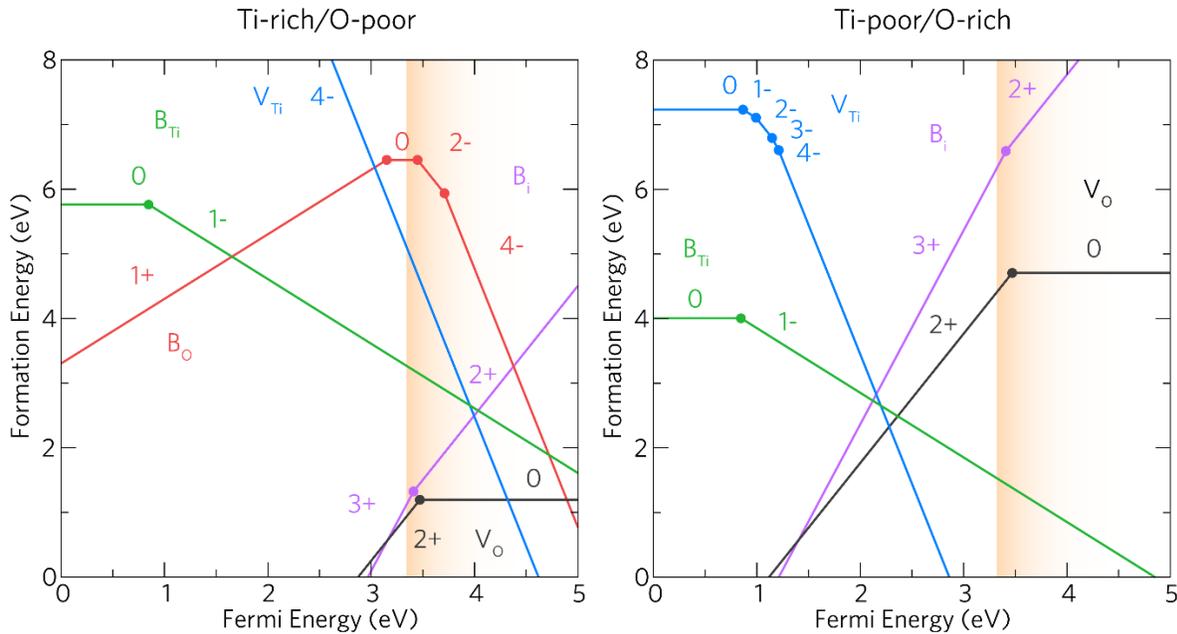


Figure 8. The transition level diagrams for $TiO_2:B$ under both *Ti-rich/O-poor* (left) and *Ti-poor/O-rich* (right) growth regimes. The Fermi energy goes from the VBM (0 eV) to 1.7 eV above the CBM (which is at 3.35 eV). The conduction band region is shown by the graded.

B_i is a three electron donor, however when it reaches the 0 and 1+ charge states (~ 2.42 eV above the CBM) (**Figure 10a and b**), the donated electrons start to become highly localized on the B and adjacent Ti atoms, this has also been seen previously by Yang *et al.*⁹⁰ the 2+ charge state is shows a delocalized electron (**Figure 10c**).

B_{Ti} has a high formation energy under *Ti-rich/O-poor* (B_{Ti}^0 occurs ~ 5.76 eV) where self-compensation is observed when B_{Ti}^{1-} crosses the B_i^{3+} line at ~ 2.12 eV above the VBM. Under *Ti-poor/O-rich* conditions, p-type defect favourable conditions, B_{Ti} is still relatively high in energy (~ 4 eV). The 1-/0 transition level occurs at ~ 0.85 eV above the VBM making this defect a *very deep* acceptor so no p-type capability should be seen.

Under *Ti-rich/O-poor* conditions, B_{Ti} begins to self-compensate ~ 2.12 eV above the VBM. Previous calculations have stated that B_{Ti} is the least favourable substitutional defect^{89,92}, however we find the opposite is true. B_{Ti}^0 distorts from the Ti site by up to $\sim 11\%$ in the b direction forming a trigonal planar BO_3 . The hole is localized on an adjacent O as shown in **Figure 10d**, with the distortion clearly visible. In the 1- charge state, the B moves back towards the original Ti site now that the hole is removed reforming a tetrahedral BO_4 .

The last defect to be considered is B_o which acts as a slightly deep donor with the 1+/0 transition level occurring at ~ 0.20 eV below the CBM. Under *Ti-rich/O-poor* conditions B_o forms at a high energy (~ 6.45 eV) and under *Ti-poor/O-rich* conditions this rises to ~ 15.23 eV. Beyond the CBM B_o quickly becomes an acceptor changing to the 2- charge

state ~ 0.1 eV above the CBM then to the 4- charge state ~ 0.36 eV above the CBM.

Under *Ti-rich/O-poor* conditions B_o becomes the dominant boron defect ~ 1.37 eV above the CBM. The partial charge density of the neutral and 4- charge states are shown in **Figures 10e and f** where localization is seen shared between the boron atom and the titanium atom below it.

Accounts by Finazzi and coworkers see an almost identical picture, however with more localization on the Ti, which could be an artifact from using a Γ -point only calculation. Less distortion is seen here than for B_{Ti} although in the neutral charge state B distorts $\sim 5\%$ in the c direction whilst the Ti below shifts $\sim 4\%$ from its original position away from the defect. The 4- charge state displays a quadruple polaron (shown in **Figure 10f**) and the atoms shift back towards their original positions ($\sim 2\%$ from B_{Ti}^0).

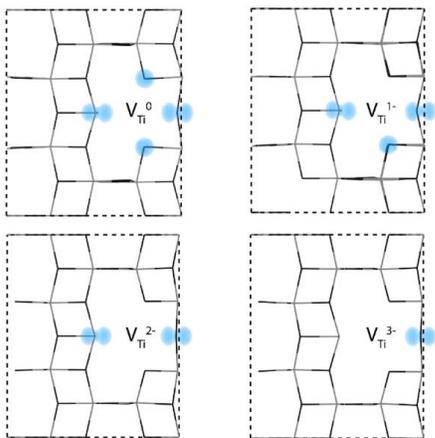


Figure 9. The partial charge densities of the charge states of V_{Ti} as viewed along the $\{010\}$ direction showing the localisation of holes (blue isosurfaces) in each example. The isosurfaces are plotted from 0 - $0.015 \text{ eV \AA}^{-3}$.

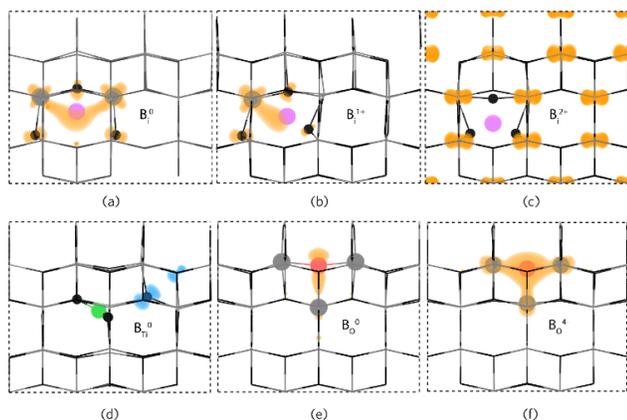


Figure 10. The partial charge densities of B_i^0 (a), B_i^{1+} (b), B_i^{2+} (c), B_{Ti}^0 (d), B_{O^0} (e) and B_{O^4} (f) defect charge states as viewed along the $\{100\}$ direction displaying the localisation of holes and electrons (blue and orange isosurfaces respectively). The isosurfaces are plotted from 0- $0.015 \text{ eV \AA}^{-3}$.

5. Conclusions:

A series of interstitial boron-doped anatase TiO_2 of different concentrations were synthesised and deposited on glass by one-step APCVD. The concentration of the dopant (from 1-5 at. % B) was varied by increasing the mass flow rate of boron isopropoxide and varying the temperature of the bubbler where it was placed. Anatase was obtained in all of the $TiO_2:B$ samples. In the case of sample C, when a higher mass flow of boron was used, rutile was formed along with a powdery deposition on top of some areas of the film. The powdery deposition was easily removed and was characterised as a mixture of anatase and a form of boric acid (H_3BO_3), called sassolite. Proved by XPS and D-SIMS, boron was incorporated in TiO_2 as interstitial, being that form the most stable of boron-doped TiO_2 .^{15,17} The incorporation of interstitial boron induced a noticeable

change in the morphology of the doped-films and in the average particle size, more remarkable in the case of sample $TiO_2:B$ (A). The optical band gap slightly changed but no visible light absorption/response was found. The photocatalytic performance of $TiO_2:B$ films under UV was enhanced, being much higher and noticeable in the case of sample A, which contains around 1 at. % B. Surprisingly, boron-doped TiO_2 samples presented certain conductivity and electron mobility, proven by multimeter and Hall Effect measurements.

From our theoretical and computational analyses, we show that in the likely event of B_i forming, the material will be made n-type under *Ti-rich/O-poor* conditions, explaining the n-type conductivity measured. B_i^{3+} is the most preferential dopant state to form. Under *Ti-poor/O-rich* conditions the Fermi level will be trapped $\sim 2 \text{ eV}$ above the VBM, indicating that electrons trapped at this level could be excited by visible light into the CBM thus increasing the visible light activity. In addition, we can conclude that an excessive addition of boron during the synthesis of the interstitial $TiO_2:B$ thin films is detrimental for the formation of the films, affecting the nucleation process and increasing the gas phase reaction that leads to a powdery deposition, as well as for the photocatalytic properties of $TiO_2:B$, which after reaching the optimal concentration (~ 1 at. %) the photocatalytic performance of the interstitial boron-doped TiO_2 samples decreases.

The data obtained by XRD, Raman spectroscopy and XPS data, indicated that: (i) boron has been implanted within the anatase phase interstitially (ii) when the mass flow of the dopant is too high the rutile phase appears and a powdery phase-mixture of TiO_2 and H_3BO_3 (sassolite) is deposited along with the film as by-products, which can be found in some areas of the substrate (glass).

ASSOCIATED CONTENT

Supporting Information. Table containing experimental parameters of the deposition, photos of the films, PXRD pattern of powdery deposition, Ti 2p environment surface XPS spectrum of sample $TiO_2:B$ (B), depth profile D-SIMS spectra of all boron-doped samples, photo of a $TiO_2:B$ thin film while testing resistance by a multimeter, FTIR spectra of the decomposition of SA in sample A and Valence Band XPS spectra of all samples. This material is available free of charge via the Internet at <http://pubs.acs.org>.

AUTHOR INFORMATION

Corresponding Author

* I. P. Parkin: i.p.parkin@ucl.ac.uk

Author Contributions

All authors have given approval to the final version of the manuscript.

Funding Sources

UCL Chemistry Department is thanked for funding and support through the grant 510300.

Notes

Any additional relevant notes should be placed here.

ACKNOWLEDGMENT

This work made use of the ARCHER UK National Supercomputing Service (<http://www.archer.ac.uk>) via our membership of the UK's HEC Materials Chemistry Consortium, which is also funded by the EPSRC (EP/L000202). The UCL Legion and Grace HPC Facilities (Legion@UCL and Grace@UCL) were also used in the completion of this work. DOS would like to acknowledge support from the EPSRC (EP/N01572X/1). Dr. F. Di Maggio, Dr. S. Sathasivam and Dr. C. Knapp are thanked for useful discussions. Dr Robert Palgrave is also thanked for access and assistance with the XPS instrument.

ABBREVIATIONS


APCVD, atmospheric pressure chemical vapour deposition, FQE, Formal quantum efficiency.

REFERENCES

- (1) Fujishima, A.; Zhang, X.; Tryk, D. A. TiO₂ Photocatalysis and Related Surface Phenomena. *Surface Science Reports*. 2008, 63, 515–582.
- (2) Kafizas, A.; Parkin, I. P. Combinatorial Atmospheric Pressure Chemical Vapor Deposition (cAPCVD): A Route to Functional Property Optimization. *J. Am. Chem. Soc.* **2011**, 133, 20458–20467.
- (3) Mills, A.; Le Hunte, S. An Overview of Semiconductor Photocatalysis. *J. Photochem. Photobiol. A Chem.* **1997**, 108, 1–35.
- (4) Velten, D.; Biehl, V.; Aubertin, F.; Valeske, B.; Possart, W.; Breme, J. Preparation of TiO₂ Layers on Cp-Ti and Ti₆Al₄V by Thermal and Anodic Oxidation and by Sol-Gel Coating Techniques and Their Characterization. *J. Biomed. Mater. Res.* **2002**, 59, 18–28.
- (5) Carlsson, J. Chemical Vapor Deposition. *Handb. Depos. Technol. Film. Coatings* **2010**, Chapter 7, 314–363.
- (6) Zaleska, A. Doped-TiO₂: A Review. *Recent Patents Eng.* **2008**, 2, 157–164.
- (7) Guillot, J.; Leccoq, E.; Duday, D.; Puhakka, E.; Riihimäki, M.; Keiski, R.; Chemin, J.-B.; Choquet, P. Combining a Molecular Modelling Approach with Direct Current and High Power Impulse Magnetron Sputtering to Develop New TiO₂ Thin Films for Antifouling Applications. *Appl. Surf. Sci.* **2015**, 333, 186–193.
- (8) Burda, C.; Chen, X.; Narayanan, R.; El-Sayed, M. A. Chemistry and Properties of Nanocrystals of Different Shapes. *Chemical Reviews*. **2005**, 105, 1025–1102.
- (9) Kafizas, A.; Kellici, S.; Darr, J. A.; Parkin, I. P. Titanium Dioxide and Composite Metal/metal Oxide Titania Thin Films on Glass: A Comparative Study of Photocatalytic Activity. *J. Photochem. Photobiol. A Chem.* **2009**, 204, 183–190.
- (10) Choy, K. Chemical Vapour Deposition of Coatings. *Prog. Mater. Sci.* **2003**, 48, 57–170.
- (11) O'Neill, S.; Parkin, I. P.; Clark, R. J. H.; Mills, A.; Elliott, N. Photocatalytically Active WO₃ Films from the Atmospheric Pressure CVD of WOCl₄ with Ethyl Acetate or Ethanol. *Chem. Vap. Depos.* **2004**, 10, 136–141.
- (12) Bhachu, D. S.; Sathasivam, S.; Sankar, G.; Scanlon, D. O.; Cibir, G.; Carmalt, C. J.; Parkin, I. P.; Watson, G. W.; Bawaked, S. M.; Obaid, A. Y.; Al-Thabaiti, S.; Basahel, S. N. Solution Processing Route to Multifunctional Titania Thin Films: Highly Conductive and Photocatalytically Active Nb:TiO₂. *Adv. Funct. Mater.* **2014**, 24, 5075–5085.
- (13) Tseng, T. K.; Lin, Y. S.; Chen, Y. J.; Chu, H. A Review of Photocatalysts Prepared by Sol-Gel Method for VOCs Removal. *Int. J. Mol. Sci.* **2010**, 11, 2336–2361.
- (14) Quesada-Cabrera, R.; Sotelo-Vazquez, C.; Darr, J. A.; Parkin, I. P. Critical Influence of Surface Nitrogen Species on the Activity of N-Doped TiO₂ Thin-Films during Photodegradation of Stearic Acid under UV Light Irradiation. *Appl. Catal. B Environ.* **2014**, 160, 582–588.
- (15) Zaleska, A.; Grabowska, E.; Sobczak, J. W.; Gazda, M.; Hupka, J. Photocatalytic Activity of Boron-Modified TiO₂ under Visible Light: The Effect of Boron Content, Calcination Temperature and TiO₂ Matrix. *Appl. Catal. B Environ.* **2009**, 89, 469–475.
- (16) Finazzi, E.; Valentin, C. Di; Pacchioni, G. Boron-Doped Anatase TiO₂: Pure and Hybrid DFT Calculations. *J. Phys. Chem. C* **2009**, 113, 220–228.
- (17) Patel, N.; Dashora, A.; Jaiswal, R.; Fernandes, R.; Yadav, M.; Kothari, D. C.; Ahuja, B. L.; Miotello, A. Experimental and Theoretical Investigations on the Activity and Stability of Substitutional and Interstitial Boron in TiO₂ Photocatalyst. *J. Phys. Chem. C* **2015**, 119, 18581–18590.
- (18) Carmichael, P.; Hazafy, D.; Bhachu, D. S.; Mills, A.; Darr, J. A.; Parkin, I. P. Atmospheric Pressure Chemical Vapour Deposition of Boron Doped Titanium Dioxide for Photocatalytic Water Reduction and Oxidation. *Phys. Chem. Chem. Phys.* **2013**, 15, 16788–16794.
- (19) Quesada-Gonzalez, M.; Boscher, N. D.; Carmalt, C. J.; Parkin, I. P. Interstitial Boron-Doped TiO₂ Thin Films: The Significant Effect of Boron on TiO₂ Coatings Grown by Atmospheric Pressure Chemical Vapor Deposition. *ACS Appl. Mater. Interfaces* **2016**, 8, 25024–25029.
- (20) O'Neill, S. A.; Parkin, I. P.; Clark, R. J. H.; Mills, A.; Elliott, N. Atmospheric Pressure Chemical Vapour Deposition of Titanium Dioxide Coatings on Glass. *J. Mater. Chem.* **2002**, 13, 56–60.
- (21) Toby, B. H. EXPGUI, a Graphical User Interface for GSAS. *J. Appl. Crystallogr.* **2001**, 34, 210–213.
- (22) Swanepoel, R. Determination of the Thickness and Optical Constants of Amorphous Silicon. *J. Phys. E Sci. Instrum.* **1983**, 16, 1214–1222.
- (23) Mills, A.; Wang, J. Simultaneous Monitoring of the Destruction of Stearic Acid and Generation of Carbon Dioxide by Self-Cleaning Semiconductor Photocatalytic Films. *J. Photochem. Photobiol. A Chem.* **2006**, 182, 181–186.
- (24) Kresse, G.; Hafner, J. Ab Initio Molecular Dynamics for Liquid Metals. *Phys. Rev. B* **1993**, 47, 558–561.
- (25) Kresse, G.; Hafner, J. Ab-Initio Molecular-Dynamics Simulation of the Liquid-Metal Amorphous-Semiconductor Transition in Germanium. *Phys. Rev. B* **1994**, 49, 14251–14269.
- (26) Kresse, G.; Furthmüller, J. Efficiency of Ab-Initio Total Energy Calculations for Metals and Semiconductors Using a Plane-Wave Basis Set. *Comput. Mater. Sci.* **1996**, 6 (1), 15–50.
- (27) Kresse, G.; Furthmu, J.; J., F.; Kresse, G.; Furthmu, J. Efficient Iterative Schemes for Ab Initio Total-Energy Calculations Using a Plane-Wave Basis Set. *Phys. Rev. B Condens. Matter Phys.* **1996**, 54, 11169.
- (28) Blochl, P. E. Projector Augmented-Wave Method. *Phys. Rev. B* **1994**, 50, 17953–17979.
- (29) Paier, J.; Marsman, M.; Hummer, K.; Kresse, G.; Gerber, I. C.; Ángyán, J. G.; Screened Hybrid Density Functionals Applied to Solids. *J. Chem. Phys.* **2006**, 124, 154709
- (30) Heyd, J.; Scuseria, G. E.; Ernzerhof, M. Hybrid Functionals Based on a Screened Coulomb Potential. *J. Chem. Phys.* **2003**, 118, 8207–8215.
- (31) Sathasivam, S.; Williamson, B. A. D.; Kafizas, A.; Althabaiti, S. A.; Obaid, A. Y.; Basahel, S. N.; Scanlon, D. O.; Carmalt, C. J.; Parkin, I. P. Computational and Experimental Study of Ta₂O₅ Thin Films. *J. Phys. Chem. C* **2017**, 121, 202–210.
- (32) Marchand, P.; Sathasivam, S.; Williamson, B. A. D.; Pugh, D.; Bawaked, S. M.; Basahel, S. N.; Obaid, A. Y.; Scanlon, D. O.; Parkin, I. P.; Carmalt, C. J. A Single-Source Precursor Approach to Solution Processed Indium Arsenide Thin Films. *J. Mater. Chem. C* **2016**, 4, 6761.
- (33) Williamson, B. A.; Buckeridge, J.; Brown, J.; Ansbro, S.;

- Palgrave, R. G.; Scanlon, D. O. Engineering Valence Band Dispersion for High Mobility P-Type Semiconductors. *Chem. Mater.* **2016**, *29*, 2402–2413.
- (34) Oba, F.; Togo, A.; Tanaka, I.; Paier, J.; Kresse, G. Defect Energetics in ZnO: A Hybrid Hartree-Fock Density Functional Study. *Phys. Rev. B - Condens. Matter Mater. Phys.* **2008**, *77*, 245202.
- (35) Chen, H.; Dawson, J. A. Nature of Nitrogen-Doped Anatase TiO₂ and the Origin of Its Visible-Light Activity. *J. Phys. Chem. C* **2015**, *119*, 15890–15895.
- (36) Kafizas, A.; Noor, N.; Carmichael, P.; Scanlon, D. O.; Carmalt, C. J.; Parkin, I. P. Combinatorial Atmospheric Pressure Chemical Vapor Deposition of F:TiO₂; The Relationship between Photocatalysis and Transparent Conducting Oxide Properties. *Adv. Funct. Mater.* **2014**, *24*, 1758–1771.
- (37) Burbano, M.; Scanlon, D. O.; Watson, G. W. Sources of Conductivity and Doping Limits in CdO from Hybrid Density Functional Theory. *J. Am. Chem. Soc.* **2011**, *133*, 15065–15072.
- (38) Rajpalke, M. K.; Linhart, W. M.; Birkett, M.; Yu, K. M.; Scanlon, D. O.; Buckeridge, J.; Jones, T. S.; Ashwin, M. J.; Veal, T. D. Growth and Properties of GaSbBi Alloys. *Appl. Phys. Lett.* **2013**, *103*, 142106.
- (39) Ganose, A. M.; Savory, C. N.; Scanlon, D. O. (CH₃NH₃)₂Pb(SCN)₂L₂: A More Stable Structural Motif for Hybrid Halide Photovoltaics? *J. Phys. Chem. Lett.* **2015**, *6*, 4594–4598.
- (40) Scanlon, D. O.; Walsh, A. Bandgap Engineering of ZnSnP₂ for High-Efficiency Solar Cells. *Appl. Phys. Lett.* **2012**, *100*, 251911.
- (41) Walsh, A.; Kehoe, A. B.; Temple, D. J.; Watson, G. W.; Scanlon, D. O. PbO₂: From Semi-Metal to Transparent Conducting Oxide by Defect Chemistry Control. *Chem. Commun. (Camb)*. **2013**, *49*, 448–450.
- (42) Buckeridge, J.; Scanlon, D. O.; Walsh, A.; Catlow, C. R. A. Automated Procedure to Determine the Thermodynamic Stability of a Material and the Range of Chemical Potentials Necessary for Its Formation Relative to Competing Phases and Compounds. *Comput. Phys. Commun.* **2014**, *185*, 330–338.
- (43) Çelik, V.; Mete, E. Range-Separated Hybrid Exchange-Correlation Functional Analyses of Anatase TiO₂ Doped with W, N, S, W/N, or W/S. *Phys. Rev. B - Condens. Matter Mater. Phys.* **2012**, *86*, 205112.
- (44) Scanlon, D. O.; Dunnill, C. W.; Buckeridge, J.; Shevlin, S. A.; Logsdail, A. J.; Woodley, S. M.; Catlow, C. R. A.; Powell, M. J.; Palgrave, R. G.; Parkin, I. P.; Watson, G. W.; Keal, T. W.; Sherwood, P.; Walsh, A.; Sokol, A. A. Band Alignment of Rutile and Anatase TiO₂. *Nat. Mater.* **2013**, *12*, 798–801.
- (45) Huy, H. A.; Aradi, B.; Frauenheim, T.; Deák, P. Calculation of Carrier-Concentration-Dependent Effective Mass in Nb-Doped Anatase Crystals of TiO₂. *Phys. Rev. B - Condens. Matter Mater. Phys.* **2011**, *83*, 155201.
- (46) Janotti, A.; Varley, J. B.; Rinke, P.; Umezawa, N.; Kresse, G.; Van de Walle, C. G. Hybrid Functional Studies of the Oxygen Vacancy in TiO₂. *Phys. Rev. B* **2010**, *8*, 85212.
- (47) Matsubara, M.; Saniz, R.; Partoens, B.; Lamoen, D. Doping Anatase TiO₂ with Group V-B and VI-B Transition Metal Atoms: A Hybrid Functional First-Principles Study. *Phys. Chem. Chem. Phys.* **2017**, *19*, 1945–1952.
- (48) Boonchun, A.; Reunchan, P.; Umezawa, N. Energetics of Native Defects in Anatase TiO₂: A Hybrid Density Functional Study. *Phys. Chem. Chem. Phys.* **2016**, *4*, 1166–1169.
- (49) Hine, N. D. M.; Frensch, K.; Foulkes, W. M. C.; Finnis, M. W. Supercell Size Scaling of Density Functional Theory Formation Energies of Charged Defects. *Phys. Rev. B - Condens. Matter Mater. Phys.* **2009**, *79*, 024112.
- (50) Nieminen, R. M. Issues in First-Principles Calculations for Defects in Semiconductors and Oxides. *Model. Simul. Mater. Sci. Eng.* **2009**, *17*, 84001.
- (51) Murphy, S. T.; Hine, N. D. M. Anisotropic charge screening and supercell size convergence of defect formation energies. **2013**, *Phys. Rev. B* *87*, 094111.
- (52) Lany, S.; Zunger, A. Assessment of Correction Methods for the Band-Gap Problem and for Finite-Size Effects in Supercell Defect Calculations: Case Studies for ZnO and GaAs. *Phys. Rev. B - Condens. Matter Mater. Phys.* **2008**, *78*, 235104.
- (53) Freysoldt, C.; Neugebauer, J.; Van De Walle, C. G. Fully Ab Initio Finite-Size Corrections for Charged-Defect Supercell Calculations. *Phys. Rev. Lett.* **2009**, *102*, 016402.
- (54) Chase, J. M. No Title. *J. Phys. Chem. Ref. Data Monogr. NIST. JANAF Thermochem. Tables* **1998**, *9*, 1.
- (55) Artiglia, L.; Lazzari, D.; Agnoli, S.; Rizzi, G. A.; Granozzi, G. Searching for the Formation of Ti – B Bonds in B - Doped TiO₂ – Rutile. **2013**, *117*, 13163–13172.
- (56) Burdett, J. K.; Hughbanks, T.; Miller, G. J.; Richardson, J. W.; Smith, J. V. Structural-Electronic Relationships in Inorganic Solids: Powder Neutron Diffraction Studies of the Rutile and Anatase Polymorphs of Titanium Dioxide at 15 and 295 K. *J. Am. Chem. Soc.* **1987**, *109*, 3639–3646.
- (57) Sabyrov, K.; Burrows, N. D.; Penn, R. L.; Merche, D.; Vandecasteele, N.; Reniers, F.; Yokoyama, T.; Kogoma, M.; Yokoyama, T.; Kogoma, M.; et al. Size-Dependent Anatase to Rutile Phase Transformation and Particle.pdf. *Chem. Mater.* **2013**, *25*, 1408–1415.
- (58) Pore, V.; Ritala, M.; Leskelä, M.; Areva, S.; Järn, M.; Järnström, J. H₂S Modified Atomic Layer Deposition Process for Photocatalytic TiO₂ Thin Films. *J. Mater. Chem.* **2007**, *17*, 1361.
- (59) Kafizas, A.; Noor, N.; Carmalt, C. J.; Parkin, I. P. TiO₂-Based Transparent Conducting Oxides; the Search for Optimum Electrical Conductivity Using a Combinatorial Approach. *J. Mater. Chem. C* **2013**, *39*, 6335.
- (60) Sotelo-Vazquez, C.; Noor, N.; Kafizas, A.; Quesada-Cabrera, R.; Scanlon, D. O.; Taylor, A.; Durrant, J. R.; Parkin, I. P. Multifunctional P-Doped TiO₂ Films: A New Approach to Self-Cleaning, Transparent Conducting Oxide Materials. *Chem. Mater.* **2015**, *27*, 3234–3242.
- (61) Evans, P.; Pemble, M. E.; Sheel, D. W. Precursor-Directed Control of Crystalline Type in Atmospheric Pressure CVD Growth of TiO₂ on Stainless Steel. *Chem. Mater.* **2006**, *18*, 5750–5755.
- (62) Buckeridge, J.; Butler, K. T.; Catlow, C. R. A.; Logsdail, A. J.; Scanlon, D. O.; Shevlin, S. A.; Woodley, S. M.; Sokol, A. A.; Walsh, A. Polymorph Engineering of TiO₂: Demonstrating How Absolute Reference Potentials Are Determined by Local Coordination. *Chem. Mater.* **2015**, *27*, 3844–3851.
- (63) Landmann, M.; Rauls, E.; Schmidt, W. G. The Electronic Structure and Optical Response of Rutile, Anatase and Brookite TiO₂. *J. Phys. Condens. Matter* **2012**, *24*, 195503.
- (64) Dou, M.; Persson, C. Comparative Study of Rutile and Anatase SnO₂ and TiO₂: Band-Edge Structures, Dielectric Functions, and Polaron Effects. *J. Appl. Phys.* **2013**, *113*, 083703.
- (65) Tang, H.; Lévy, F.; Berger, H.; Schmid, P. E. Urbach Tail of Anatase TiO₂. *Phys. Rev. B* **1995**, *52*, 7771–7774.
- (66) Patrick, C. E.; Giustino, F. GW Quasiparticle Bandgaps of Anatase TiO₂ Starting from DFT + U. *J. physics. Condens. matter* **2012**, *24*, 202201.
- (67) Kang, W.; Hybertsen, M. S. Quasiparticle and Optical Properties of Rutile and Anatase TiO₂. *Phys. Rev. B - Condens. Matter Mater. Phys.* **2010**, *82*, 085203.

- (68) Gong, S.; Liu, B.-G. Electronic Structures and Optical Properties of TiO₂: Improved Density-Functional-Theory Investigation. *Chinese Phys. B* **2012**, *21*, 57104.
- (69) Chiodo, L.; Salazar, M.; Romero, A. H.; Laricchia, S.; Della Sala, F.; Rubio, A. Structure, Electronic, and Optical Properties of TiO₂ Atomic Clusters: An Ab Initio Study. *J. Chem. Phys.* **2011**, *135*, 244704.
- (70) Morgan, B. J.; Watson, G. W. Intrinsic N-Type Defect Formation in TiO₂: A Comparison of Rutile and Anatase from GGA+U Calculations. *J. Phys. Chem. C* **2010**, *114*, 2321–2328.
- (71) Mattioli, G.; Alippi, P.; Filippone, F.; Caminiti, R.; Amore Bonapasta, A. Deep versus Shallow Behavior of Intrinsic Defects in Rutile and Anatase TiO₂ Polymorphs. *J. Phys. Chem. C* **2010**, *114*, 21694–21704.
- (72) Deák, P.; Aradi, B.; Frauenheim, T. Polaronic Effects in TiO₂ Calculated by the HSE06 Hybrid Functional: Dopant Passivation by Carrier Self-Trapping. *Phys. Rev. B - Condens. Matter Mater. Phys.* **2011**, *83*, 155207.
- (73) Morgan, B. J.; Watson, G. W. Polaronic Trapping of Electrons and Holes by Native Defects in Anatase TiO₂. *Phys. Rev. B - Condens. Matter Mater. Phys.* **2009**, *80*, 233102.
- (74) Oba, F.; Nishitani, S. R.; Isotani, S.; Adachi, H.; Tanaka, I. Energetics of Native Defects in ZnO. *J. Appl. Phys.* **2001**, *90*, 824–828.
- (75) Janotti, A.; Van De Walle, C. G. Native Point Defects in ZnO. *Phys. Rev. B - Condens. Matter Mater. Phys.* **2007**, *76*, 165202.
- (76) Agoston, P.; Albe, K.; Nieminen, R. M.; Puska, M. J. Intrinsic N-Type Behavior in Transparent Conducting Oxides: A Comparative Hybrid-Functional Study of In₂O₃, SnO₂, and ZnO. *Phys. Rev. Lett.* **2009**, *103*, 245501.
- (77) Scanlon, D. O.; Watson, G. W. On the Possibility of P-Type SnO₂. *J. Mater. Chem.* **2012**, *22*, 25236–25245.
- (78) Kılıç, C.; Zunger, A. Origins of Coexistence of Conductivity and Transparency in SnO₂. *Phys. Rev. Lett.* **2002**, *88*, 95501.
- (79) Singh, A. K.; Janotti, A.; Scheffler, M.; Van De Walle, C. G. Sources of Electrical Conductivity in SnO₂. *Phys. Rev. Lett.* **2008**, *101*, 055502.
- (80) Walsh, A.; Catlow, C. R. A.; Sokol, A. A.; Woodley, S. M. Physical Properties, Intrinsic Defects, and Phase Stability of Indium Sesquioxide. *Chem. Mater.* **2009**, *21*, 4962–4969.
- (81) Ágoston, P.; Albe, K. Formation Entropies of Intrinsic Point Defects in Cubic In₂O₃ from First-Principles Density Functional Theory Calculations. *Phys. Chem. Chem. Phys.* **2009**, *11*, 3226.
- (82) Lany, S.; Zunger, A. Polaronic Hole Localization and Multiple Hole Binding of Acceptors in Oxide Wide-Gap Semiconductors. *Phys. Rev. B - Condens. Matter Mater. Phys.* **2009**, *80*, 085202.
- (83) Goyal, A.; Gorai, P.; Peng, H.; Lany, S.; Stevanović, V. A Computational Framework for Automation of Point Defect Calculations. *Comput. Mater. Sci.* **2017**, *130*, 1–9.
- (84) Scanlon, D. O. Defect Engineering of BaSnO₃ for High-Performance Transparent Conducting Oxide Applications. *Phys. Rev. B - Condens. Matter Mater. Phys.* **2013**, *87*, 161201.
- (85) Deák, P.; Aradi, B.; Frauenheim, T. Quantitative Theory of the Oxygen Vacancy and Carrier Self-Trapping in Bulk TiO₂. *Phys. Rev. B - Condens. Matter Mater. Phys.* **2012**, *86*, 195206.
- (86) Deák, P.; Aradi, B.; Frauenheim, T. Oxygen Deficiency in TiO₂: Similarities and Differences between the Ti Self-Interstitial and the O Vacancy in Bulk Rutile and Anatase. *Phys. Rev. B - Condens. Matter Mater. Phys.* **2015**, *92*, 045204.
- (87) Na-Phattalung, S.; Smith, M. F.; Kim, K.; Du, M. H.; Wei, S. H.; Zhang, S. B.; Limpijumngong, S. First-Principles Study of Native Defects in Anatase TiO₂. *Phys. Rev. B - Condens. Matter Mater. Phys.* **2006**, *73*, 125205.
- (88) Dixon S. C.; Sathasivam S.; Williamson B. A. D.; Scanlon, D. O.; Carmalt C. J.; Parkin I. P. Transparent Conducting N-Type ZnO:Sc-Synthesis, Optoelectronic Properties and Theoretical Insight. *J. Mater. Chem. C* **2017**, *5*, 7585.
- (89) Zhao, W.; Ma, W.; Chen, C.; Zhao, J.; Shuai, Z. Efficient Degradation of Toxic Organic Pollutants with Ni₂O₃/TiO₂-XBX under Visible Irradiation. *J. Am. Chem. Soc.* **2004**, *126*, 4782–4783.
- (90) Yang, K.; Dai, Y.; Huang, B. Origin of the Photoactivity in Boron-Doped Anatase and Rutile TiO₂ Calculated from First Principles. *Phys. Rev. B - Condens. Matter Mater. Phys.* **2007**, *76*, 195201.
- (91) Gombac, V.; De Rogatis, L.; Gasparotto, A.; Vicario, G.; Montini, T.; Barreca, D.; Balducci, G.; Fornasiero, P.; Tondello, E.; Graziani, M. TiO₂ Nanopowders Doped with Boron and Nitrogen for Photocatalytic Applications. *Chem. Phys.* **2007**, *339*, 111–123.
- (92) Geng, H.; Yin, S.; Yang, X.; Shuai, Z.; Liu, B. Geometric and Electronic Structures of the Boron-Doped Photocatalyst TiO₂. *J. Phys. Condens. Matter* **2006**, *18*, 87–96.
- (93) Li, L.; Meng, F.; Hu, X.; Qiao, L.; Sun, C. Q.; Tian, H.; Zheng, W. TiO₂ Band Restructuring by B and P Dopants. *PLoS One* **2016**, *11*, 152726.

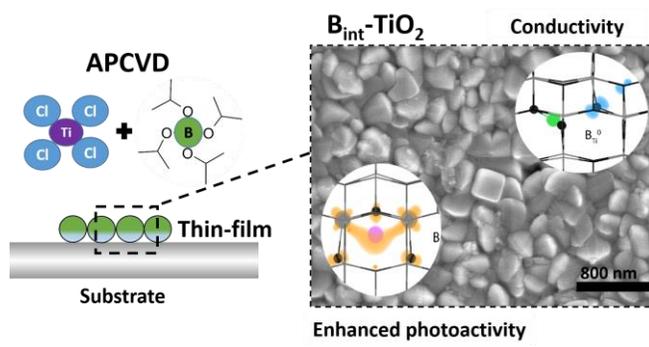

TOC Graphic