



Zitierweise:

Internationale Ausgabe: doi.org/10.1002/anie.202102570

Deutsche Ausgabe: doi.org/10.1002/ange.202102570

# The Electrophilicity of Surface Carbon Species in the Redox Reactions of CuO-CeO<sub>2</sub> Catalysts

Liqun Kang<sup>+</sup>, Bolun Wang<sup>+,\*</sup>, Andreas T. Güntner, Siyuan Xu, Xu hao Wan, Yiyun Liu, Sushila Marlow, Yifei Ren, Diego Gianolio, Chiu C. Tang, Vadim Murzin, Hiroyuki Asakura, Qian He, Shaoliang Guan, Juan J. Velasco-Vélez, Sotiris E. Pratsinis, Yuzheng Guo and Feng Ryan Wang\*

**Abstract:** Electronic metal–support interactions (EMSI) describe the electron flow between metal sites and a metal oxide support. It is generally used to follow the mechanism of redox reactions. In this study of CuO-CeO<sub>2</sub> redox, an additional flow of electrons from metallic Cu to surface carbon species is observed via a combination of operando X-ray absorption spectroscopy, synchrotron X-ray powder diffraction, near ambient pressure near edge X-ray absorption fine structure spectroscopy, and diffuse reflectance infrared Fourier transform spectroscopy. An electronic metal–support–carbon interaction (EMSCI) is proposed to explain the reaction pathway of CO oxidation. The EMSCI provides a complete picture of the mass and electron flow, which will help predict and improve the catalytic performance in the selective activation of CO<sub>2</sub>, carbonate, or carbonyl species in CI chemistry.

## Introduction

The interaction between metals and supports plays a vital role in modulating the catalytic performance of active sites. Concepts such as SMSI<sup>[1]</sup> and EMSI<sup>[2]</sup> are well-established to describe the geometric,<sup>[3]</sup> electronic<sup>[2b–d,4]</sup> and bifunctional<sup>[5]</sup> modification of active sites from the support. With respect to

the electronic interaction, there is a flow of electrons either from a metallic centre to an oxidative support or from a reductive support to an oxidative metal centre. The net electron flow leads to modified electronic structures of the active centre and its surroundings, and thus to different behaviours in the adsorption and activation of reaction molecules compared to its unperturbed state. In addition to the oxide support, the destination of the electron flow can also be the surface carbon species resulting from the decomposition and deposition from carbonaceous reactants. Carbon atoms, with nine oxidation states and an electronegativity of 2.55, can accept electrons from metals. Carbon materials are widely used as electron acceptors in lithium-ion batteries<sup>[6]</sup> and organic photovoltaics.<sup>[7]</sup> There are some representative studies in catalysis find electrons are transferred from metal to carbon,<sup>[8]</sup> especially in electrocatalysis.<sup>[9]</sup> Reduction of carbon can form metal-carbon species in Fischer-Tropsch synthesis<sup>[10]</sup> and alkynes hydrogenation.<sup>[11]</sup> A CO<sub>2</sub><sup>δ-</sup> species is formed when the 2π<sub>u</sub> orbital of surface CO<sub>2</sub> accepts electrons from metallic Cu.<sup>[12]</sup> Theoretical calculations also predict the modification of the Cu electronic structure via surface carbons.<sup>[13]</sup>

[\*] L. Kang,<sup>[†]</sup> Dr. B. Wang,<sup>[†]</sup> Y. Liu, S. Marlow, Y. Ren, Dr. F. R. Wang  
Department of Chemical Engineering, University College London  
London WC1E 7JE (UK)  
E-Mail: bolun.wang@ucl.ac.uk  
ryan.wang@ucl.ac.uk

Dr. A. T. Güntner, Prof. S. E. Pratsinis  
Particle Technology Laboratory, Institute of Process Engineering  
Department of Mechanical and Process Engineering  
ETH Zürich, 8092 Zürich (Switzerland)

Dr. D. Gianolio, Dr. C. C. Tang  
Diamond Light Source Ltd  
Harwell Science and Innovation Campus  
Didcot, Oxfordshire OX11 0DE (UK)

Dr. V. Murzin  
Deutsches Elektronen Synchrotron DESY  
22607 Hamburg (Germany)

Dr. H. Asakura  
Department of Molecular Engineering  
Graduate School of Engineering, Kyoto University  
Kyotodaigaku Katsura, Nishikyoku, Kyoto 6158510 (Japan)

Dr. Q. He  
Department of Materials Science and Engineering  
National University of Singapore  
Singapore, 117575 (Singapore)

Dr. S. Guan  
HarwellXPS—The EPSRC National Facility for Photoelectron Spectroscopy, Research Complex at Harwell (RCaH)  
Didcot OX11 0FA (UK)

Dr. J. J. Velasco-Vélez  
Fritz-Haber-Institut der Max-Planck-Gesellschaft  
Faradayweg 4–6, 14195 Berlin (Germany)

S. Xu, X. Wan, Dr. Y. Guo  
School of Electrical Engineering and Automation  
Wuhan University, Wuhan (China)


[†] These authors contributed equally to this work.

Supporting information and the ORCID identification numbers for some of the authors of this article can be found under:  
<https://doi.org/10.1002/anie.202102570>.

© 2021 The Authors. Angewandte Chemie published by Wiley-VCH GmbH. This is an open access article under the terms of the Creative Commons Attribution License, which permits use, distribution and reproduction in any medium, provided the original work is properly cited.

Cu has moderate adsorption strength for carbonaceous intermediates,<sup>[14]</sup> and is widely used for C1 chemistry, including CO oxidation,<sup>[15]</sup> water-gas shift,<sup>[16]</sup> steam reforming,<sup>[17]</sup> methanol synthesis,<sup>[18]</sup> and electrochemical reduction of CO<sub>2</sub>.<sup>[14,19]</sup> The well-documented Ce<sup>4+</sup>/Ce<sup>3+</sup> redox pair enables the transfer of oxygen atoms and electrons between Cu<sup>2+</sup>/Cu<sup>+</sup>/Cu<sup>0</sup> active sites and the CeO<sub>2</sub> support.<sup>[20]</sup> Validation of this catalytic cycle still requires precise quantification of their oxidation states to match the balance of electron transfer.<sup>[21]</sup> Here we report the full picture of electron transfer in this system by considering the electrophilicity of surface carbon species, which are in situ deposited from CO molecules. At 453 K, electrons are initially enriched on metallic Cu via CO reduction (*CO stage*) to build up the chemical potential for an electron flow within the catalyst. The electrophilicity of surface carbon species is then studied in an inert atmosphere (*He stage*) to exclude electron transfer from or to the gaseous molecules. Finally, O<sub>2</sub> is used to extract electrons that are originally injected into the catalyst from CO (*O<sub>2</sub> stage*). The CO oxidation activity of the catalyst at individual stage is compared below 353 K to elucidate the impact of initial oxidation states of Cu and Ce as well as the surface carbon species.

In a full cycle of CO oxidation, electrons are transferred from CO to Cu, then to Ce and carbon (Figure 1) and finally to O<sub>2</sub>. We therefore extend the concept of EMSI to „electronic metal-support-carbon interactions“ (EMSCI) in order to address this interplay among Cu, Ce and carbon species.

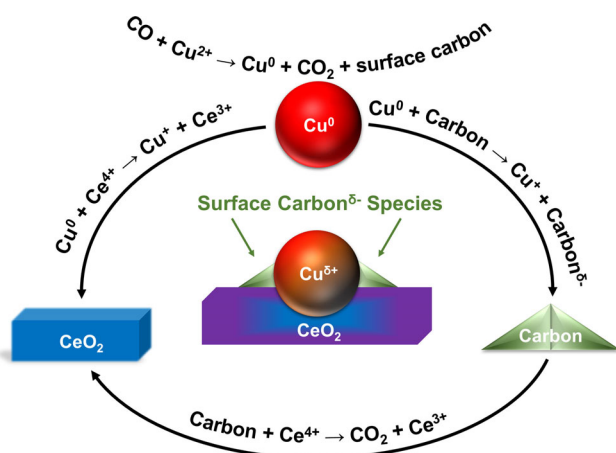

**Figure 1.** Schematic of the electronic metal–support–carbon interactions (EMSCI) among Cu<sup>0</sup>, CeO<sub>2</sub>, and surface carbon species. The models are simplified to illustrate the major structural changes of the sample. Surface carbon species are represented by the shaded green triangles. They are located on the surface of Cu and CeO<sub>2</sub>, as well as at the interface.

## Results and Discussion

### Highly Dispersed CuO Clusters on CeO<sub>2</sub>

Fine powder of highly dispersed 20 wt % CuO clusters on CeO<sub>2</sub> with 71 m<sup>2</sup>g<sup>-1</sup> specific surface area were prepared via


flame spray pyrolysis.<sup>[20b,22]</sup> The high-resolution aberration-corrected high angle annular dark field-scanning transmission electron microscopy (HAADF-STEM) images show crystalline CeO<sub>2</sub> particles with an average size of around 6 nm (Figure S1f,g). The corresponding energy-dispersive X-ray spectroscopy (EDS) maps identify the presence of Cu in the form of ca. 5 nm particles surrounded by CeO<sub>2</sub> (Figure S1a-e). The X-ray photoelectron spectroscopy (XPS) shows that ca. 18% of the Ce is Ce<sup>3+</sup>, indicating a considerable number of oxygen vacancies in the lattice (Figure S2 and Table S1).<sup>[23]</sup> The surface Cu/(Cu + Ce) ratio determined by XPS is 0.36, which is close to the theoretical bulk Cu/(Cu + Ce) ratio (0.35) for 20 wt % CuO-CeO<sub>2</sub>. This indicates good dispersion of the Cu species over CeO<sub>2</sub>, leading to large Cu/Ce interface. In comparison, Cu species are usually enriched on CeO<sub>2</sub> surface using conventional synthesis methods, showing much higher surface Cu content compared to the bulk composition (Table S2).<sup>[24]</sup> Laboratory X-ray diffraction (XRD) pattern shows broadened CeO<sub>2</sub> diffraction peaks (Figure S3a), whereas weak CuO diffraction peaks can be recognised by synchrotron X-ray powder diffraction (SXPD; Figure S3b). Therefore, the initial catalyst structure of 5 nm CuO and 6 nm CeO<sub>2</sub> is confirmed with 18% Ce<sup>3+</sup> present.

This 20 wt % CuO-CeO<sub>2</sub> catalyst has been applied for the preferential CO oxidation in the presence of 50% H<sub>2</sub>, achieving a wide temperature window from 377 to 388 K with 99% conversion and selectivity of CO oxidation.<sup>[20b]</sup> Our previous in situ study used a sequence of CO/N<sub>2</sub>/O<sub>2</sub> flows at 453 K to probe the change of Cu oxidation state and the corresponding gas profile.<sup>[20b]</sup> Two interesting phenomena were observed: 1) under inert N<sub>2</sub>, Cu<sup>0</sup> was slowly reoxidised; 2) when N<sub>2</sub> was changed to O<sub>2</sub>, CO<sub>2</sub> was released without an external CO feed. In addition, the near ambient pressure-near-edge X-ray absorption fine structure (NAP-NEXAFS) spectra of a similar system reveals the conversion from oxidised carbon species (288.3 eV) to reduced carbon species (284.9 eV) in ultra-high vacuum (Figure S4). We hypothesise that carbon species will deposit on the surface of CuO-CeO<sub>2</sub> from gas-phase CO. Such carbon species are reduced under inert conditions, whereas Cu<sup>0</sup> is oxidised simultaneously. When O<sub>2</sub> is introduced, the carbon species are oxidised to CO<sub>2</sub>. This hypothesis of EMSCI is verified via a combination of operando X-ray absorption fine structure (XAFS), SXPD, NAP-NEXAFS, diffuse reflectance infrared Fourier transform spectroscopy (DRIFTS) and gas component quantification at the CO, He and O<sub>2</sub> stages, as presented below.

### CO Stage: Electron Transfer from CO to Cu

Introducing CO at 453 K to the catalyst reduces Cu<sup>2+</sup> and Ce<sup>4+</sup> (Figure 2). Most of the Cu reduction follows the sequence of Cu<sup>2+</sup> → Cu<sup>+</sup> → Cu<sup>0</sup>, as indicated in the Cu K-edge X-ray absorption near edge structure (XANES) and SXPD (Figure 2a,b). The Ce<sup>3+</sup> content increases from 20% to 24% according to the peak fitting results of the Ce L<sub>3</sub>-edge XANES (Figure 2c, note that the initial 20% Ce<sup>3+</sup> content is slightly different from the 18% Ce<sup>3+</sup> obtained from XPS study).



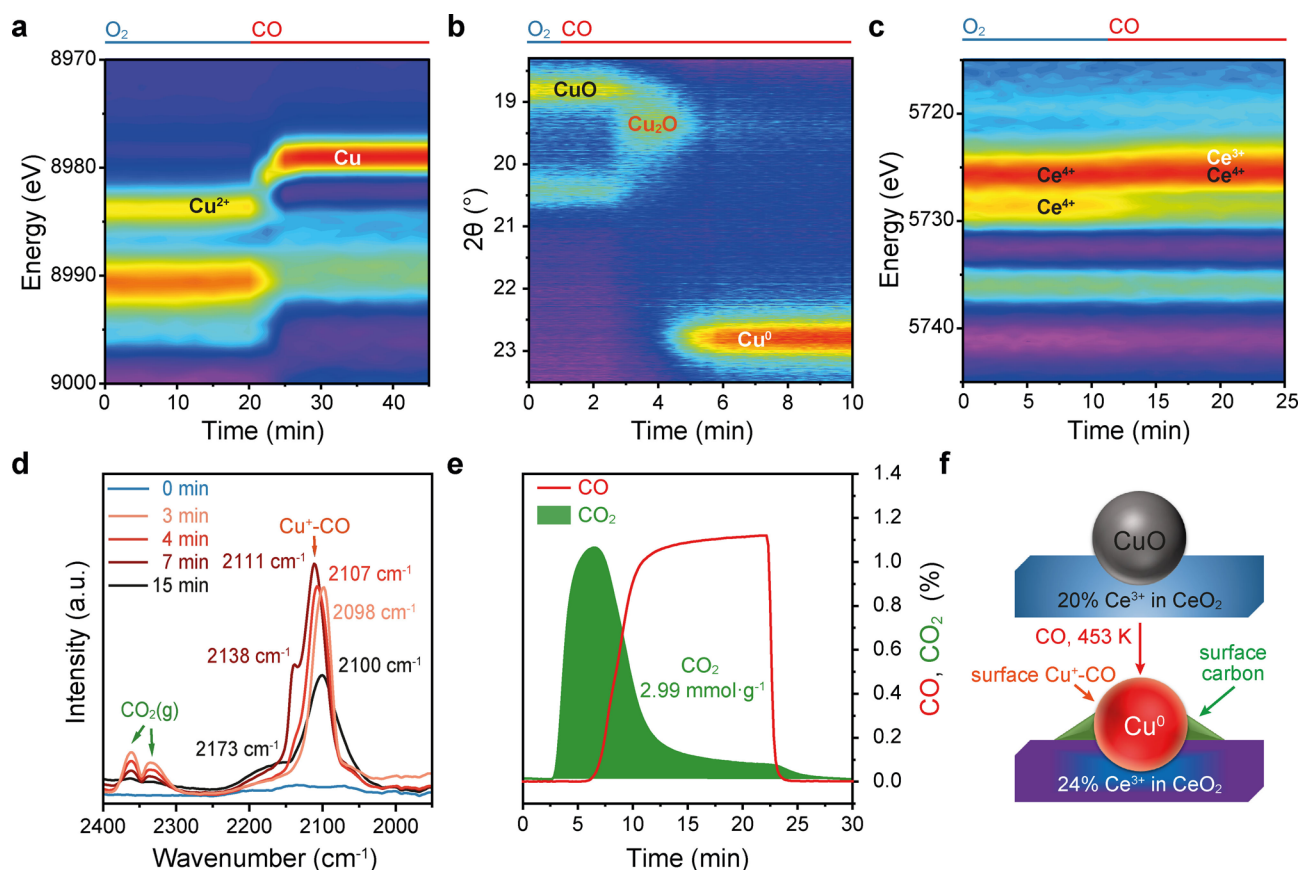

**Figure 2.** Operando characterisation of Cu, Ce and surface carbon during the reduction of CO by CuO-CeO<sub>2</sub> at 453 K. a) Contour map of the Cu K-edge first derivative XANES spectra, showing the reduction of Cu<sup>2+</sup> to Cu<sup>0</sup>. XANES spectra are shown in Figure S5. b) Contour map of the SXP patterns, showing the conversion of CuO to metallic Cu. The SXP patterns are shown in Figure S7. c) Contour map of the Ce L<sub>3</sub>-edge first derivative XANES spectra, showing the increase of Ce<sup>3+</sup> content after reduction. XANES spectra are shown in Figure S8 and their fitting results are given in Table S3. d) DRIFTS spectra of the surface carbonyl species from CO adsorption. The initial spectrum obtained in O<sub>2</sub> at 453 K is labelled as 0 min (blue curve) and the progress in CO at 453 K is colour coded from light pink to black. e) Exhaust gas profile of the CO reduction. The 80 mg sample was pre-oxidised in 20% O<sub>2</sub> then purged with N<sub>2</sub> at 453 K. f) Simplified models of the structural evolution from CuO-CeO<sub>2</sub> to Cu<sup>0</sup>-CeO<sub>2</sub>.

DRIFTS shows the absorption peaks of Cu<sup>+</sup>-carbonyl species (Cu<sup>+</sup>-CO) in the range of 2160–2080 cm<sup>-1</sup>,<sup>[25]</sup> suggesting the presence of Cu<sup>+</sup> on the surface of metallic Cu (Figure 2d). NAP-NEXAFS at the Cu L<sub>3</sub>-edge validates that Cu<sup>+</sup> dominates the surface layer after the reduction of CuO (Figure S10). Such surface Cu<sup>+</sup> species on Cu<sup>0</sup> clusters over CeO<sub>2</sub> have also been reported in the water gas shift reaction.<sup>[16]</sup> In general, the surface CO absorption band undergoes a slight blue shift from 2098 to 2111 cm<sup>-1</sup>, and then a red shift to 2100 cm<sup>-1</sup> with a significant intensity decrease. The initial blue shift indicates the increase of CO coverage<sup>[25]</sup> on Cu<sup>+</sup> along with the release of CO<sub>2</sub> detected at 2364 and 2337 cm<sup>-1</sup>. A new shoulder peak at 2138 cm<sup>-1</sup> appears when the CO coverage is maximised. The peak is similar to the reported band at 2135 cm<sup>-1</sup> of CO on partially reduced CuO<sub>x</sub>.<sup>[25b]</sup> The increase of a broad feature between 1700–1200 cm<sup>-1</sup> (Figure S11 from blue to dark red) that corresponds to surface carbonate species is observed.<sup>[16b,26]</sup> The formation of the carbonate stems from the oxidation of surface carbonyl species, a process that is reported in the literature.<sup>[16b]</sup> These carbonates can increase the electrophilicity of neighbour Cu<sup>+</sup>,<sup>[25a]</sup> leading to a broad absorption band of Cu<sup>+</sup>-CO at

2173 cm<sup>-1</sup> when the reduction of Cu is complete as reflected by the disappearance of CO<sub>2</sub> peaks (Figure 2d). The second stage red-shift to the steady and broadened band centred at 2100 cm<sup>-1</sup> corresponds to a combination of Cu<sup>+</sup>-CO and Cu<sup>0</sup>-CO bands at 2160–2080 cm<sup>-1</sup> and 2090–2060 cm<sup>-1</sup>, respectively.<sup>[25]</sup> A slight decline in surface carbonate species is observed (Figure S11 from dark red to black).

The CO reduction of 20 wt% CuO-CeO<sub>2</sub> releases 2.99 mmol g<sup>-1</sup> of CO<sub>2</sub> at 453 K (Figure 2e). Theoretically, the complete reduction from Cu<sup>2+</sup> to Cu<sup>0</sup> will generate 2.52 mmol g<sup>-1</sup> of CO<sub>2</sub>. Furthermore, there is a 4% reduction of Ce<sup>4+</sup> to Ce<sup>3+</sup> (according to XANES fitting) results in 0.09 mmol g<sup>-1</sup> of CO<sub>2</sub> formation. These results indicate an additional 0.38 mmol g<sup>-1</sup> CO<sub>2</sub> generation that is not related to the Cu and Ce redox. According to the literature, this additional CO<sub>2</sub> may come from the disproportionation of CO.<sup>[27]</sup> A very recent work on CO<sub>2</sub> methanation also finds that the presence of Ce<sup>3+</sup> can also help dissociate CO and CO<sub>2</sub>, leading to diverse carbon species.<sup>[28]</sup> Carbonyls and carbonates are detected by DRIFTS, suggesting the high complexity of those surface carbon species. (Figure 2d and Figure S11).


The combination of operando XAFS of the Cu and Ce oxidation states, SXPD of small crystalline clusters and DRIFTS of surface carbon species reveals the change of Cu, Ce and C during the *CO stage* (Figure 2 f). The majority of CuO is fast reduced to metallic Cu with a trace amount of surface Cu<sup>+</sup>, whereas 4% Ce<sup>4+</sup> is reduced to Ce<sup>3+</sup>. Surface carbon species (i.e., carbonyls and carbonates) are deposited from gaseous CO.

### He Stage: Electron Transfer from Cu<sup>0</sup> to Ce<sup>4+</sup> and Surface Carbon

The inert He flow enables observation of the internal reaction among Cu<sup>0</sup>, Ce<sup>3+</sup>/Ce<sup>4+</sup> and surface carbon species. Cu<sup>0</sup> clusters are immediately oxidised to Cu<sup>+</sup> once CO is replaced by He (Figure 3 a,b). Simultaneously, 9% Ce<sup>4+</sup> is reduced to Ce<sup>3+</sup> (Figure 3 c). These results suggest a fast redox reaction [Eq. (1)].



To the best of our knowledge, the observation of Cu oxidation and Ce reduction here is the first direct evidence for this reaction, proving the EMSI between Cu and Ce. The Cu<sup>+</sup> state is stable in the He flow (Figure 3 a), whereas the crystalline Cu<sub>2</sub>O feature gradually decreases with time at 453 K, suggesting the amorphization of Cu<sub>2</sub>O (Figure 3 b). The oxidation of all Cu<sup>0</sup> to Cu<sup>+</sup> would require 54% Ce<sup>4+</sup> to be reduced to Ce<sup>3+</sup>, which is much higher than the 9% formation of Ce<sup>3+</sup>. Within the system, the only destination to receive the additional electrons from Cu<sup>0</sup> are surface carbon species with their abundant valence states, given that both carbonyl species and carbonate species are present on Cu<sup>+</sup>-CeO<sub>2</sub> at the *He stage* (Figure 3 d, Figure S15). The blue shift from 2100 cm<sup>-1</sup> to 2127 cm<sup>-1</sup> suggests the increased electrophilicity of Cu due to its oxidation. The surface carbon species as electron acceptors have also been reported for CO<sub>2</sub> activation on metallic Cu, where CO<sub>2</sub><sup>δ-</sup> species were formed via electron transfer from Cu<sup>0</sup> into the 2π<sub>u</sub> orbital of surface CO<sub>2</sub>.<sup>[12]</sup> Such CO<sub>2</sub><sup>δ-</sup> species were identified by surface enhanced Raman spectroscopy<sup>[29]</sup> and XPS.<sup>[30]</sup> In addition, the decomposition of

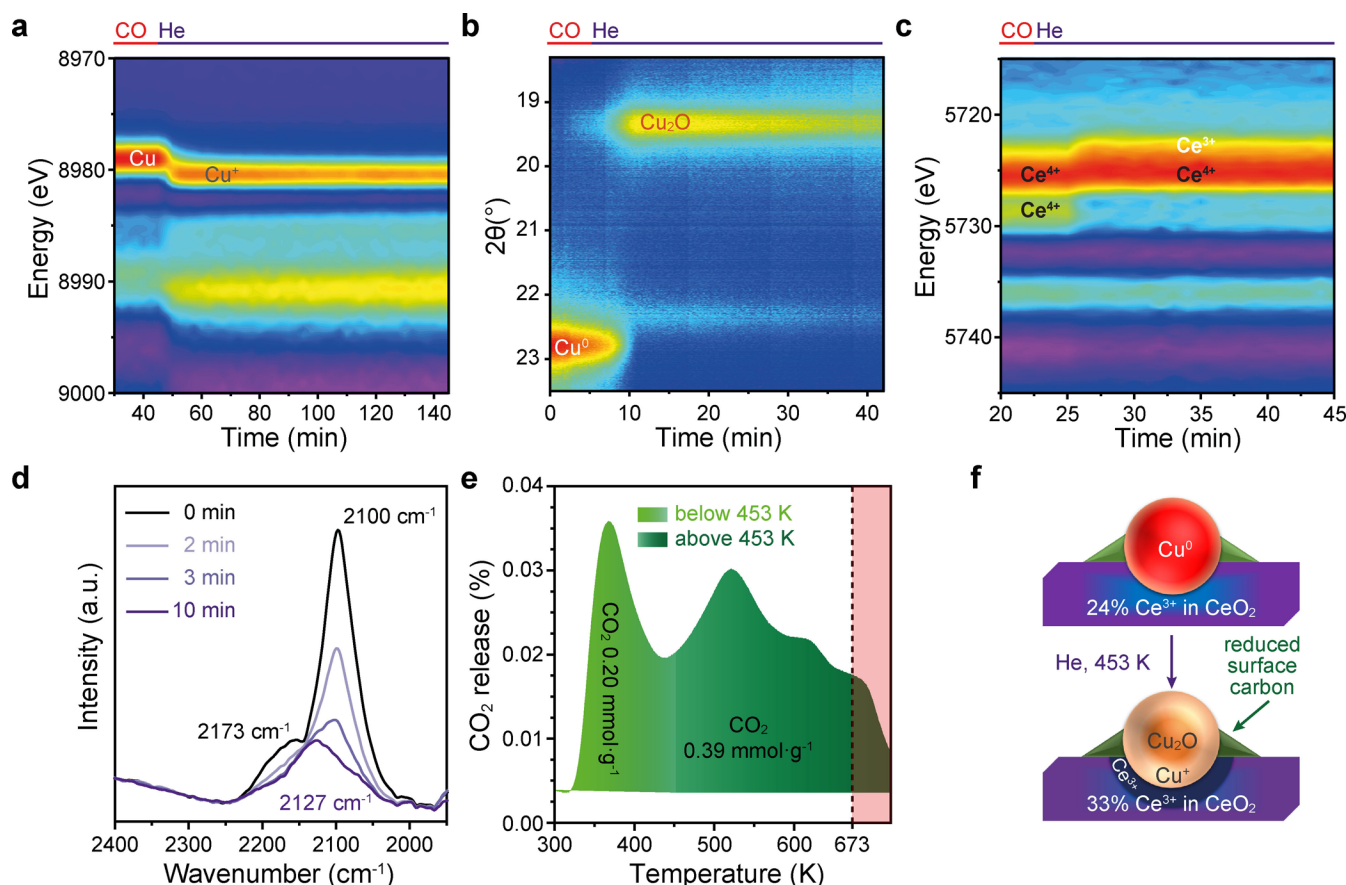

**Figure 3.** Operando characterisation of Cu, Ce and surface carbon during the internal reaction of Cu<sup>0</sup>-CeO<sub>2</sub> at 453 K in He. a) Contour map of the Cu K-edge first derivative XANES spectra, showing the oxidation of Cu<sup>0</sup> to Cu<sup>+</sup>. XANES spectra are shown in Figure S12. b) Contour map of the SXPD patterns, showing the conversion of metallic Cu to Cu<sub>2</sub>O and the following amorphization of Cu<sub>2</sub>O. SXPD patterns are shown in Figure S13. c) Contour map of the Ce L<sub>3</sub>-edge first derivative XANES spectra, showing the further increase of Ce<sup>3+</sup> content by accepting electrons from Cu<sup>0</sup>. XANES spectra are shown in Figure S14 and their fitting results are given in Table S3. d) DRIFTS spectra of the surface carbonyl species after CO desorption. The initial spectrum obtained in CO at 453 K is labelled as 0 min (black curve) and the progress in He at 453 K is colour coded from light violet to purple. e) Exhaust gas profile during TPD from 300 K to 673 K, then holding at 673 K for 30 min indicated by the pink-shaded region. The CO released during TPD is negligible. f) Simplified models of the structural evolution from Cu<sup>0</sup>-CeO<sub>2</sub> to Cu<sup>+</sup>-CeO<sub>2</sub>.




these carbon species can generate surface O atoms to form Cu–O bond.<sup>[26,31]</sup>

The flow of electrons from Cu<sup>0</sup> to Ce<sup>4+</sup> and surface carbon species under inert atmosphere proves the EMSCI concept (Figure 3 f). Temperature programmed desorption (TPD) is applied to support the presence of those surface carbon species at 453 K in addition to the DRIFTS evidence. To obtain a similar metallic Cu and CeO<sub>2</sub> surface, the catalyst is reduced first with CO at 453 K and then cooled to 298 K under the CO atmosphere. Subsequent heating in He leads to CO<sub>2</sub> desorption. The released CO<sub>2</sub> may come from the decomposition of surface carbonates<sup>[26]</sup> or the desorption of CO<sub>2</sub> formed during CO reduction.<sup>[31]</sup> 0.20 mmol g<sup>-1</sup> and 0.39 mmol g<sup>-1</sup> of CO<sub>2</sub> release are observed below and above 453 K, respectively (Figure 3 e). The latter is stable under He in the in situ study and is partially responsible for the oxidation of Cu (Figure 3 a,b). The remaining surface carbon species that cannot be desorbed by heating in He may also accept electrons and oxidise Cu. Density functional theory (DFT) calculations with Bader charge analysis are performed to evaluate the electron transfer between Cu<sup>0</sup> and adsorbed carbon species. Each Cu atom that adsorbs CO has extra +0.11e and +0.12e at low

and high CO coverages, respectively whereas each CO molecule gains -0.13e from Cu (Figure S16, S17 and Table S4). When the coverage of carbon species is further increased, the adsorbed carbon atoms, the number of which equals to half of the Cu atoms, gain -16.58e from Cu, resulting in +0.20e to +0.70e on individual Cu atom (Figure S18). The theoretical calculations results validate the electrophilicity of surface carbon species and its impact on reducing the electron density of Cu. An O<sub>2</sub> stage is then carried out to study those residual carbon and the further oxidation of Cu<sup>+</sup>/Ce<sup>3+</sup>.

#### O<sub>2</sub> Stage: Electron Transfer from Ce<sup>4+</sup>, Surface Carbon, and Cu<sup>+</sup> to O<sub>2</sub>

When switching to O<sub>2</sub> at 453 K, the Ce<sup>3+</sup> content recovers to the initial level, whereas only a slight increase of Cu<sup>2+</sup> is found (Figure 4 a,c). No significant change is found in SXPD, suggesting Cu<sup>+</sup> remains amorphous (Figure 4 b). While the majority of Cu remains in Cu<sup>+</sup> state, a full reoxidation to Cu<sup>2+</sup> is found on the surface as indicated in the NAP-NEXAFS (Figure S22). A possible explanation is that a dense layer of

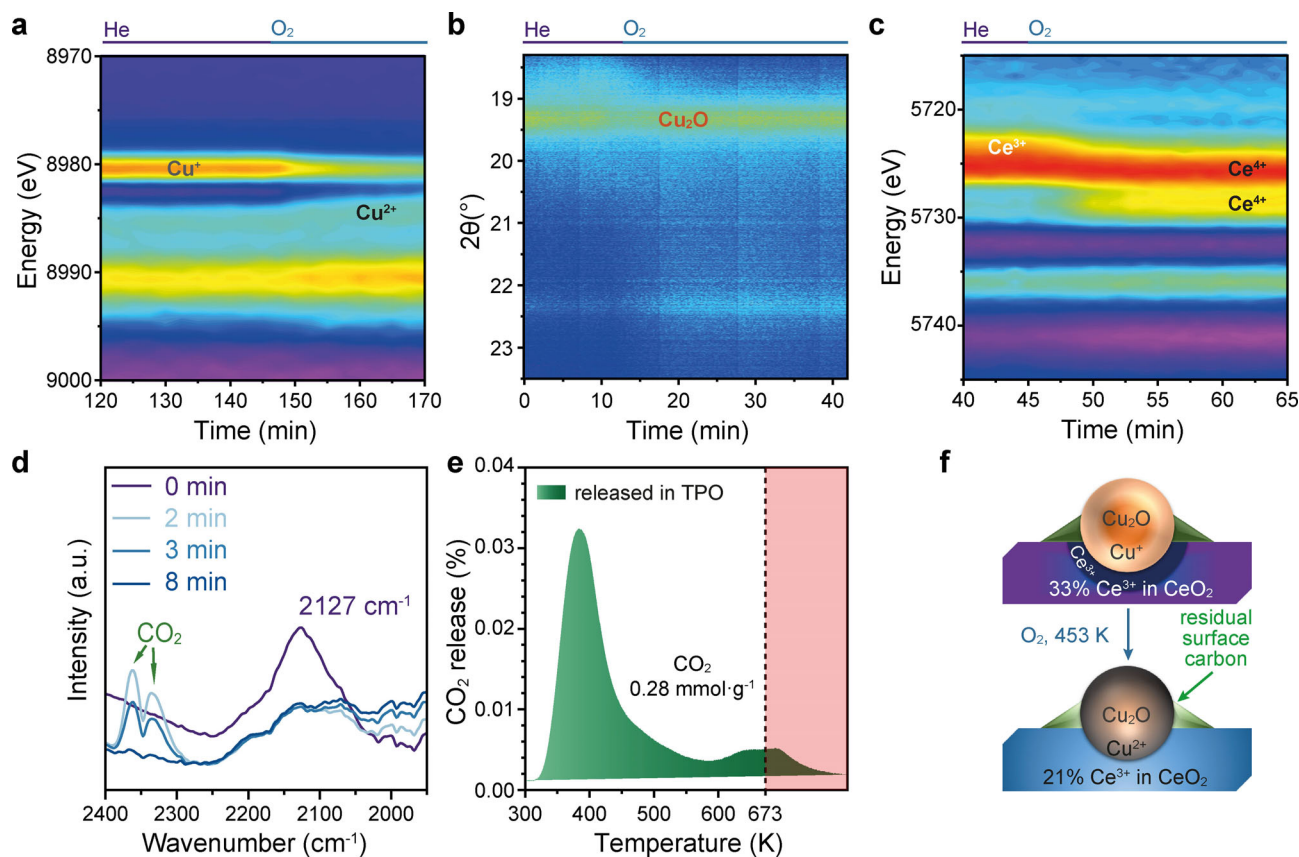

**Figure 4.** Operando characterisation of Cu, Ce and surface carbon during the oxidation of Cu<sup>+</sup>-CeO<sub>2</sub> at 453 K with O<sub>2</sub>. a) Contour map of the Cu K-edge first derivative XANES spectra, showing the incomplete oxidation of Cu<sup>+</sup> to Cu<sup>2+</sup>. XANES spectra are shown in Figure S19. b) Contour map of the SXPD patterns, showing the crystalline Cu<sub>2</sub>O preserved during oxidation. SXPD patterns are shown in Figure S20. c) Contour map of the Ce L<sub>3</sub> edge first derivative XANES spectra, showing the recovery of Ce<sup>3+</sup> content after oxidation. XANES spectra are shown in Figure S21 and their fitting results are given in Table S3. d) DRIFTS spectra of the surface carbonyl species as they are oxidised and released as CO<sub>2</sub>. The initial spectrum obtained in He at 453 K is labelled in purple and the progress in O<sub>2</sub> at 453 K is colour coded from light blue to blue. e) Exhaust gas profile shows the released CO<sub>2</sub> during TPO from 300 K to 673 K, then holding at 673 K for 30 min indicated by the pink-shaded region. f) Simplified models of the structural evolution from Cu<sup>+</sup>-CeO<sub>2</sub> to Cu<sup>+</sup>/Cu<sup>2+</sup>-CeO<sub>2</sub>.

CuO is formed over the Cu<sub>2</sub>O surface, preventing further oxidation of Cu<sup>+</sup>. We hypothesise that when the size of the Cu<sub>2</sub>O decreases, the curvature of the surface CuO layer increases and more Cu can be oxidised into Cu<sup>2+</sup>. An extreme case is the atomic Cu sites, which can be completely oxidised back to Cu<sup>2+</sup> even under He flow.<sup>[22]</sup>

The residual surface carbonyl species with a band at 2137 cm<sup>-1</sup> are removed via oxidation with simultaneously released CO<sub>2</sub> (Figure 4d,f), whereas the carbonates only slightly decrease under O<sub>2</sub> at 453 K (Figure S23). In addition to the 0.59 mmol g<sup>-1</sup> CO<sub>2</sub> released during TPD in He up to 673 K (Figure 3e), temperature programmed oxidation (TPO) of the residual surface carbon can further generate 0.28 mmol g<sup>-1</sup> CO<sub>2</sub> (Figure 4e). Therefore, at least 0.87 mmol g<sup>-1</sup> of carbon species can be deposited and 0.67 mmol g<sup>-1</sup> of them can contribute to the oxidation of Cu<sup>0</sup> via EMSCI. The amount of carbon deposited on the surface may be directly proportional to the CO pressure (*P*<sub>CO</sub>). The different *P*<sub>CO</sub> in each experiment may lead to small inconsistencies in the carbon deposition as well as the time required for achieving steady states (Table S5). Nevertheless, the general picture on the direction of the electron flow via EMSCI is valid.

#### CO Oxidation Kinetics at Four Stages of Electron Flow

EMSCI describes the flow of electrons in the sequence of 1) CO; 2) Cu<sup>0</sup>; 3) carbon + Ce<sup>3+</sup>; 4) O<sub>2</sub>. At these four stages, the Cu oxidation states are Cu<sup>2+</sup>, Cu<sup>0</sup>, Cu<sup>+</sup> and Cu<sup>+</sup>/Cu<sup>2+</sup>, respectively. The CO oxidation kinetics is then studied at these four stages (Figure S24) to understand the influence of surface carbon and Cu species in catalysis.

The reaction temperature is controlled below 353 K to preserve the initial states of the catalysts. The distinct CO conversion profiles (Figure 5a) indicate the different catalytic behaviours at each stage. In general, the CO oxidation activity of the initial Cu species on CeO<sub>2</sub> follows the order Cu<sup>2+</sup> > Cu<sup>+</sup> > Cu<sup>0</sup>. The fully oxidised CuO-CeO<sub>2</sub> shows the highest turnover frequency (TOF) at 323 K and lowest apparent ac-


tivation energy (*E*<sub>a</sub>) (Figure 5b,c blue) whereas the Cu<sup>0</sup>-CeO<sub>2</sub> shows the lowest activity and increased *E*<sub>a</sub> (Figure 5b,c red). The Cu<sup>0</sup>-CeO<sub>2</sub> catalysts separately reduced by CO and H<sub>2</sub> show similar TOF and *E*<sub>a</sub> in the kinetic region (Figure 5b,c red and wine). However, the CO-reduced catalyst with considerable amount of surface carbon shows much higher activity in the high conversion region compared to the H<sub>2</sub>-reduced catalyst which is free of carbon (Figure 5a red and wine). It suggests that surface carbon on Cu<sup>0</sup> species is irrelevant to the activity in the kinetic region but can significantly promote the reaction in the high conversion region. After the CO-reduced Cu<sup>0</sup>-CeO<sub>2</sub> is annealed in He, the obtained Cu<sup>+</sup> with reduced surface carbon shows increased TOF (Figure 5). The obtained Cu<sup>+</sup> cannot be fully oxidised to the initial Cu<sup>2+</sup> in 20% O<sub>2</sub>/He at 473 K, thus the activity cannot fully recover although its *E*<sub>a</sub> significantly decreases (Figure 5a,c navy with open symbol).

The Ce<sup>3+</sup> content is generally accepted to be inversely proportional to thermodynamic oxygen vacancy formation energy (*E*<sub>vac</sub>)<sup>[23]</sup> which is regarded as a descriptor for CO oxidation activity.<sup>[32]</sup> Unfortunately, there is no clear relationship between the Ce<sup>3+</sup> content and CO oxidation performance can be correlated in this work. It suggests that influence of Ce<sup>3+</sup> content towards CO oxidation is not as obvious as that of the Cu oxidation state.

In conclusion, the lower oxidation state of Cu species on CeO<sub>2</sub> leads to inferior CO oxidation activity. Surface carbon is irrelevant to the activity in the kinetic region but can significantly promote the reaction in the high conversion region.

#### Conclusion

The concept of EMSCI is established to describe the electron flow for the CuO-CeO<sub>2</sub> system during CO oxidation. More specifically, the electrons flow from CO to Cu, then to Ce and surface carbon species, and finally to O<sub>2</sub>. The EMSCI concept sheds light on the catalytic cycle of other CO and CO<sub>2</sub> involved reactions promoted by polyvalent metal oxides. The probability of transition metals transferring the *d* electrons to

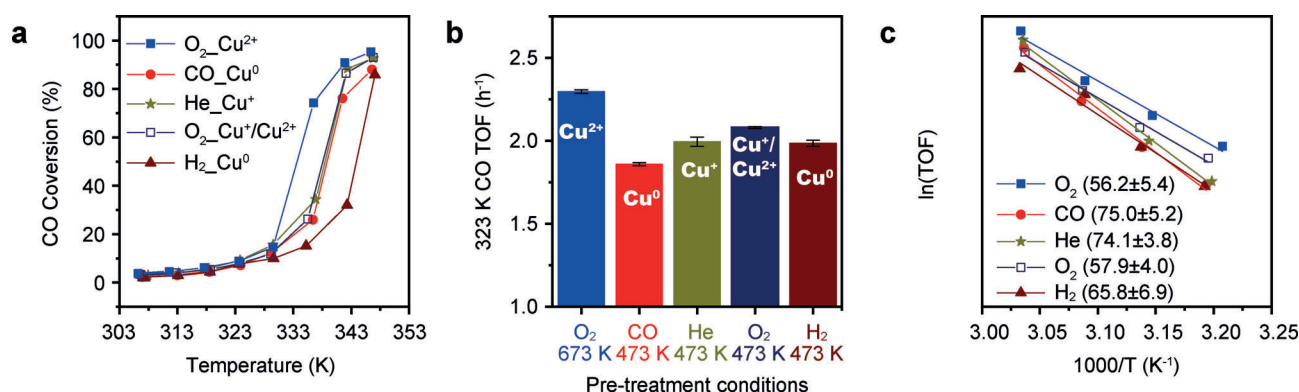

**Figure 5.** The catalytic performance of 20 wt% CuO-CeO<sub>2</sub> in CO oxidation after different pretreatments. CO oxidation conditions: Weight hourly space velocity (WHSV) per gram of catalyst: 1500 mL<sub>CO</sub> h<sup>-1</sup>·g<sup>-1</sup>. 80 mg 20 wt% CuO-CeO<sub>2</sub>, 200 mL min<sup>-1</sup> flow, 1% CO, 10% O<sub>2</sub>, He balanced. a) Conversion of CO as a function of temperature and catalysed by the catalysts with different Cu oxidation states: Cu<sup>2+</sup> (Stage 1, blue solid squares); Cu<sup>0</sup> (Stage 2, red circles); Cu<sup>+</sup> (Stage 3, dark yellow stars); Cu<sup>+</sup>/Cu<sup>2+</sup> (Stage 4, navy open squares); H<sub>2</sub>-reduced Cu<sup>0</sup> (dark red triangles). b) CO TOF at 323 K. c) Arrhenius plots in the range of 313–328 K. The calculated *E*<sub>a</sub> values (kJ mol<sup>-1</sup>) are listed in parentheses.



the  $\pi^*$  orbitals of surface carbon species will govern how CO<sub>2</sub> or CO can be activated over the catalysts.

## Acknowledgements

The project is funded by EPSRC (EP/P02467X/1 and EP/S018204/1), Royal Society (RG160661, IES\R3\170097, IES\R1\191035, IEC\R3\193038), the Newton International Fellowship (NF170761). We acknowledge Helmholtz-Zentrum Berlin for the beamtime in BESSY II (Germany) (18207435-ST, 19108389-ST). We acknowledge SPring-8 (Japan) for the *operando* XAFS experiments conducted under the proposal no. 2019A1533. Parts of this research were carried out at P64/PETRA III at DESY (Germany) (I-20190358), a member of the Helmholtz Association (HGF). The research leading to this result has been supported by the project CALIPSOplus under the Grant Agreement 730872 from the EU Framework Programme for Research and Innovation HORIZON 2020. We acknowledge the 8A2 beamline of the Pohang Accelerator Laboratory (Korea) for NAP-NEXAFS experiment (2019-3rd-8A2-005). We acknowledge electron Physical Science Imaging Centre at Diamond Light Source (DLS, UK) for the STEM experiment (Proposal No. MG24450, MG22776, MG22572, MG20643 and MG17559). We acknowledge the B18 and I20-EDE beamline of DLS for XAFS experiment (Proposal No. SP17377, SP20629 and SP20939). We acknowledge the I11 beamline of DLS for SXP experiment (Proposal No. NT15763). We acknowledge the B07-C beamline of DLS for NAP-NEXAFS experiment (Proposal No. SI24197). We thank the DLS for the award of beamtime at B18 beamline as part of the UK Catalysis Hub Block Allocation Group (Proposal No. SP15151) and Energy Materials Block Allocation Group (Proposal No. SP14239). The UK Catalysis Hub is kindly thanked for resources and support provided via our membership of the UK Catalysis Hub Consortium and funded by EPSRC (grants EP/K014706/2, EP/K014668/1, EP/K014854/1, EP/K014714/1 and EP/M013219/1). The authors would like to thank the Research Complex for access and support to these facilities and equipment. XPS data collection was performed at the EPSRC National Facility for XPS ('HarwellXPS'), operated by Cardiff University and University College London, under contract No. PR16195. The present work is dedicated to the memory of Prof. Dangsheng Su (01.07.1961–24.06.2019) who had worked on carbocatalysis for his whole life.

## Conflict of interest

The authors declare no conflict of interest.

**Stichwörter:** CO oxidation · copper-ceria · electrophilicity · EMSI · surface chemistry

- [1] a) S. J. Tauster, S. C. Fung, R. L. Garten, *J. Am. Chem. Soc.* **1978**, *100*, 170–175; b) D. E. Resasco, R. S. Weber, S. Sakellson, M. McMillan, G. L. Haller, *J. Phys. Chem.* **1988**, *92*, 189–193; c) C.-

- J. Pan, M.-C. Tsai, W.-N. Su, J. Rick, N. G. Akalework, A. K. Agegnehu, S.-Y. Cheng, B.-J. Hwang, *J. Taiwan Inst. Chem. Eng.* **2017**, *74*, 154–186; d) P. Wu, S. Tan, J. Moon, Z. Yan, V. Fung, N. Li, S.-Z. Yang, Y. Cheng, C. W. Abney, Z. Wu, A. Savara, A. M. Momen, D.-e. Jiang, D. Su, H. Li, W. Zhu, S. Dai, H. Zhu, *Nat. Commun.* **2020**, *11*, 3042.
- [2] a) C. T. Campbell, *Nat. Chem.* **2012**, *4*, 597–598; b) P. Hu, Z. Huang, Z. Amghouz, M. Makkee, F. Xu, F. Kapteijn, A. Dikhtiarenko, Y. Chen, X. Gu, X. Tang, *Angew. Chem. Int. Ed.* **2014**, *53*, 3418–3421; *Angew. Chem.* **2014**, *126*, 3486–3489; c) S. D. Senanayake, J. A. Rodriguez, D. Stacchiola, *Top. Catal.* **2013**, *56*, 1488–1498; d) A. Bruix, J. A. Rodriguez, P. J. Ramirez, S. D. Senanayake, J. Evans, J. B. Park, D. Stacchiola, P. Liu, J. Hrbek, F. Illas, *J. Am. Chem. Soc.* **2012**, *134*, 8968–8974; e) M. Kon-solakis, *Appl. Catal. B* **2016**, *198*, 49–66; f) J. A. Farmer, C. T. Campbell, *Science* **2010**, *329*, 933–936.
- [3] a) J. Zhang, M. Zhang, Z. Jin, J. Wang, Z. Zhang, *Appl. Surf. Sci.* **2012**, *258*, 3991–3999; b) J. Sá, J. Bernardi, J. A. Anderson, *Catal. Lett.* **2007**, *114*, 91–95; c) T. Komaya, A. T. Bell, Z. Wengsieh, R. Gronsky, F. Engelke, T. S. King, M. Pruski, *J. Catal.* **1994**, *149*, 142–148; d) Q. Fu, T. Wagner, S. Olliges, H.-D. Carstensen, *J. Phys. Chem. B* **2005**, *109*, 944–951; e) Y. Gao, Y. Liang, S. A. Chambers, *Surf. Sci.* **1996**, *365*, 638–648.
- [4] a) D. W. Goodman, *Catal. Lett.* **2005**, *99*, 1–4; b) A. W. Grant, C. T. Campbell, *Phys. Rev. B* **1997**, *55*, 1844–1851; c) J. A. Horsley, *J. Am. Chem. Soc.* **1979**, *101*, 2870–2874.
- [5] a) K. Hayek, R. Kramer, Z. Paál, *Appl. Catal. A* **1997**, *162*, 1–15; b) C. M. Kalamaras, P. Panagiotopoulou, D. I. Kondarides, A. M. Efsthathiou, *J. Catal.* **2009**, *264*, 117–129; c) F. Raimondi, G. G. Scherer, R. Kötz, A. Wokaun, *Angew. Chem. Int. Ed.* **2005**, *44*, 2190–2209; *Angew. Chem.* **2005**, *117*, 2228–2248.
- [6] J. B. Goodenough, Y. Kim, *Chem. Mater.* **2010**, *22*, 587–603.
- [7] a) A. Pivrikas, N. S. Sariciftci, G. Juška, R. Österbacka, *Prog. Photovoltaics* **2007**, *15*, 677–696; b) N. Tessler, Y. Preezant, N. Rappaport, Y. Roichman, *Adv. Mater.* **2009**, *21*, 2741–2761.
- [8] a) J. Graciani, K. Mudiyansele, F. Xu, A. E. Baber, J. Evans, S. D. Senanayake, D. J. Stacchiola, P. Liu, J. Hrbek, J. Fernandez Sanz, J. A. Rodriguez, *Science* **2014**, *345*, 546–550; b) E. T. C. Vogt, B. M. Weckhuysen, *Chem. Soc. Rev.* **2015**, *44*, 7342–7370.
- [9] X.-L. Lu, X. Rong, C. Zhang, T.-B. Lu, *J. Mater. Chem. A* **2020**, *8*, 10695–10708.
- [10] a) T. Herranz, S. Rojas, F. J. Pérez-Alonso, M. Ojeda, P. Terreros, J. L. G. Fierro, *J. Catal.* **2006**, *243*, 199–211; b) E. de Smit, F. Cinquini, A. M. Beale, O. V. Safonova, W. van Beek, P. Sautet, B. M. Weckhuysen, *J. Am. Chem. Soc.* **2010**, *132*, 14928–14941.
- [11] a) D. Teschner, E. Vass, M. Hävecker, S. Zafeirotas, P. Schnörch, H. Sauer, A. Knop-Gericke, R. Schlögl, M. Chamam, A. Wootsch, A. S. Canning, J. J. Gamman, S. D. Jackson, J. McGregor, L. F. Gladden, *J. Catal.* **2006**, *242*, 26–37; b) D. Teschner, J. Borsodi, A. Wootsch, Z. Révay, M. Hävecker, A. Knop-Gericke, S. D. Jackson, R. Schlögl, *Science* **2008**, *320*, 86–89.
- [12] M. Favaro, H. Xiao, T. Cheng, W. A. Goddard, J. Yano, E. J. Crumlin, *Proc. Natl. Acad. Sci. USA* **2017**, *114*, 6706–6711.
- [13] a) O. Piqué, I. Z. Koleva, F. Viñes, H. A. Aleksandrov, G. N. Vayssilov, F. Illas, *Angew. Chem. Int. Ed.* **2019**, *58*, 1744–1748; *Angew. Chem.* **2019**, *131*, 1758–1762; b) B. Martínez, O. Piqué, H. Prats, F. Viñes, F. Illas, *Appl. Surf. Sci.* **2020**, *513*, 145765.
- [14] M. B. Ross, P. De Luna, Y. F. Li, C. T. Dinh, D. Kim, P. Yang, E. H. Sargent, *Nat. Catal.* **2019**, *2*, 648–658.
- [15] a) C. S. Polster, H. Nair, C. D. Baertsch, *J. Catal.* **2009**, *266*, 308–319; b) H. Yen, Y. Seo, S. Kaliaguine, F. Kleitz, *Angew. Chem. Int. Ed.* **2012**, *51*, 12032–12035; *Angew. Chem.* **2012**, *124*, 12198–12201; c) R. Kydd, W. Y. Teoh, K. Wong, Y. Wang, J. Scott, Q.-H. Zeng, A.-B. Yu, J. Zou, R. Amal, *Adv. Funct. Mater.* **2009**, *19*, 369–377; d) D. Gamarra, G. Munuera, A. B. Hungria, M.



- Fernández-García, J. C. Conesa, P. A. Midgley, X. Q. Wang, J. C. Hanson, J. A. Rodriguez, A. Martínez-Arias, *J. Phys. Chem. C* **2007**, *111*, 11026–11038.
- [16] a) X. Wang, J. A. Rodriguez, J. C. Hanson, D. Gamarra, A. Martínez-Arias, M. Fernández-García, *J. Phys. Chem. B* **2006**, *110*, 428–434; b) A. L. Cámara, S. Chansai, C. Hardacre, A. Martínez-Arias, *Int. J. Hydrogen Energy* **2014**, *39*, 4095–4101.
- [17] a) T. Nishiguchi, T. Matsumoto, H. Kanai, K. Utani, Y. Matsu-mura, W.-J. Shen, S. Imamura, *Appl. Catal. A* **2005**, *279*, 273–277; b) J. Papavasiliou, G. Avgouropoulos, T. Ioannides, *Appl. Catal. B* **2009**, *88*, 490–496.
- [18] a) J. A. Rodriguez, P. Liu, D. J. Stacchiola, S. D. Senanayake, M. G. White, J. G. Chen, *ACS Catal.* **2015**, *5*, 6696–6706; b) S. Kattel, P. J. Ramirez, J. G. Chen, J. A. Rodriguez, P. Liu, *Science* **2017**, *355*, 1296–1299.
- [19] a) C. T. Dinh, T. Burdyny, M. G. Kibria, A. Seifitokaldani, C. M. Gabardo, F. P. G. de Arquer, A. Kiani, J. P. Edwards, P. De Luna, O. S. Bushuyev, C. Q. Zou, R. Quintero-Bermudez, Y. J. Pang, D. Sinton, E. H. Sargent, *Science* **2018**, *360*, 783–787; b) D. Wakerley, S. Lamaison, F. Ozanam, N. Menguy, D. Mercier, P. Marcus, M. Fontecave, V. Mougél, *Nat. Mater.* **2019**, *18*, 1222–1227.
- [20] a) S. Y. Yao, K. Mudiyansele, W. Q. Xu, A. C. Johnston-Peck, J. C. Hanson, T. P. Wu, D. Stacchiola, J. A. Rodriguez, H. Y. Zhao, K. A. Beyer, K. W. Chapman, P. J. Chupas, A. Martínez-Arias, R. Si, T. B. Bolin, W. J. Liu, S. D. Senanayake, *ACS Catal.* **2014**, *4*, 1650–1661; b) F. Wang, R. Büchel, A. Savitsky, M. Zalibera, D. Widmann, S. E. Pratsinis, W. Lubitz, F. Schüth, *ACS Catal.* **2016**, *6*, 3520–3530.
- [21] T. E. James, S. L. Hemmingson, T. Ito, C. T. Campbell, *J. Phys. Chem. C* **2015**, *119*, 17209–17217.
- [22] L. Kang, B. Wang, Q. Bing, M. Zalibera, R. Büchel, R. Xu, Q. Wang, Y. Liu, D. Gianolio, C. C. Tang, E. K. Gibson, M. Danaie, C. Allen, K. Wu, S. Marlow, L.-d. Sun, Q. He, S. Guan, A. Savitsky, J. J. Velasco-Vélez, J. Callison, C. W. M. Kay, S. E. Pratsinis, W. Lubitz, J.-y. Liu, F. R. Wang, *Nat. Commun.* **2020**, *11*, 4008.
- [23] a) J. Paier, C. Penschke, J. Sauer, *Chem. Rev.* **2013**, *113*, 3949–3985; b) E. W. McFarland, H. Metiu, *Chem. Rev.* **2013**, *113*, 4391–4427.
- [24] G. Avgouropoulos, T. Ioannides, H. Matralis, *Appl. Catal. B Environ.* **2005**, *56*, 87–93.
- [25] a) K. I. Hadjiivanov, G. N. Vayssilov, *Adv. Catal.* **2002**, *47*, 307–511; b) J. Schumann, J. Kröhnert, E. Frei, R. Schlögl, A. Trunschke, *Top. Catal.* **2017**, *60*, 1735–1743.
- [26] M. S. Spencer, *Surf. Sci.* **1995**, *339*, L897–L901.
- [27] a) A. Holmgren, B. Andersson, D. Duprez, *Appl. Catal. B* **1999**, *22*, 215–230; b) C. Li, Y. Sakata, T. Arai, K. Domen, K. Maruya, T. Onishi, *J. Chem. Soc. Chem. Commun.* **1991**, 410–411.
- [28] A. Parastaev, V. Muravev, E. Huertas Osta, A. J. F. van Hoof, T. F. Kimpel, N. Kosinov, E. J. M. Hensen, *Nat. Catal.* **2020**, *3*, 526–533.
- [29] M. Pohl, A. Otto, *Surf. Sci.* **1998**, *406*, 125–137.
- [30] X. Deng, A. Verdaguer, T. Herranz, C. Weis, H. Bluhm, M. Salmeron, *Langmuir* **2008**, *24*, 9474–9478.
- [31] P. B. Rasmussen, P. A. Taylor, I. Chorkendorff, *Surf. Sci.* **1992**, *269*, 352–359.
- [32] J. S. Elias, K. A. Stoerzinger, W. T. Hong, M. Risch, L. Giordano, A. N. Mansour, Y. Shao-Horn, *ACS Catal.* **2017**, *7*, 6843–6857.

Manuskript erhalten: 19. Februar 2021

Akzeptierte Fassung online: 17. März 2021

Endgültige Fassung online: ■ ■ ■ ■ ■ ■ ■ ■ ■ ■




## Forschungsartikel



## Surface Chemistry

L. Kang, B. Wang,\* A. T. Güntner, S. Xu,  
X. Wan, Y. Liu, S. Marlow, Y. Ren,  
D. Gianolio, C. C. Tang, V. Murzin,  
H. Asakura, Q. He, S. Guan,  
J. J. Velasco-Vélez, S. E. Pratsinis, Y. Guo,  
F. R. Wang\* ————— ■■■■—■■■■

The Electrophilicity of Surface Carbon  
Species in the Redox Reactions of CuO-  
CeO<sub>2</sub> Catalysts

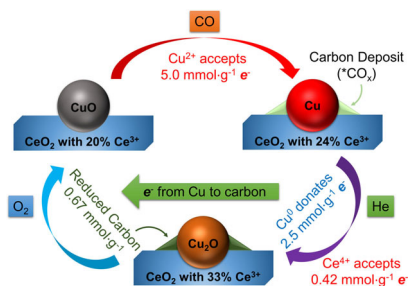

During the oxidation of CO over the surface of a CuO-CeO<sub>2</sub> catalyst, electrons are simultaneously transferred from Cu<sup>0</sup> to lattice Ce<sup>4+</sup> and surface carbon species deposited from CO. These „electronic metal–support–carbon interactions“ (EMSCI) are thought to play an important role in the reactions involving the support and surface carbon species in C1 chemistry.

