

Spin-strain coupling in $\text{NiCl}_2\cdot 4\text{SC}(\text{NH}_2)_2$

O. Chiatti¹, A. Sytcheva¹, J. Wosnitza¹, S. Zherlitsyn¹

A. A. Zvyagin², V. S. Zapf³, M. Jaime³, and A. Paduan-Filho⁴


¹ Dresden High Magnetic Field Laboratory, FZD, Germany; ² B.Verkin Institute for Low Temperature Physics and Engineering of the NAS of Ukraine, Kharkov, Ukraine; ³ National High Magnetic Field Laboratory (NHMFL), Los Alamos National Laboratory (LANL), New Mexico, USA; ⁴ Instituto de Física, Universidade de São Paulo, Brazil

Motivation

- Direct probing of spin-phonon interaction
- Study the influence of quantum critical points on the phonon degrees of freedom
- Experimental test for the magnetic spin models of low-dimensional magnets

Structure and properties of Dichloro-tetrakis-Thiourea-Nickel (II), or DTN

- Body-centered tetragonal crystal structure
- Ni^{2+} : $S = 1$ spin-chains along the c axis
- Single-ion anisotropy $D = 8.9$ K; exchange parameters: intra-chain $J_c = 2.2$ K; inter-chain $J_{a,b} = 0.18$ K [2,3]
- Gap in magnetic excitations dominated by D



Simplified structure of DTN: the $S = 1$ spins of the Ni ions form chains along the c direction. From Ref. 4.

- There are two quantum critical points: $H_c \approx 2.1$ T and $H_s \approx 12.6$ T
- For $T_N^{\text{max}} < 1.2$ K and $H_c < H < H_s$: 3D long-range order (canted XY-AFM) [1,2]
- Magnetostriction along the spin-chains: $\Delta L/L < 10^{-4}$ [4]

Experimental results

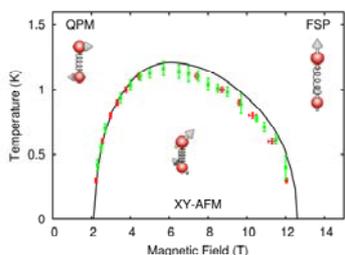


Fig. 1: Phase diagram of DTN for magnetic fields parallel to the c direction. The green and red dots are obtained from the ultrasonic measurements presented here, the solid line depicts results from Ref. [3]. The inserted drawings depict the model from Ref. [4].

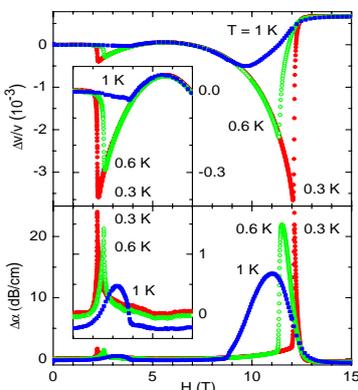


Fig. 2: Relative change of sound velocity and attenuation of the c_{33} -mode at 78 MHz, as a function of magnetic field along the c axis for $T < T_N^{\text{max}}$. The insets show the curves close to H_c with an enlarged scale.

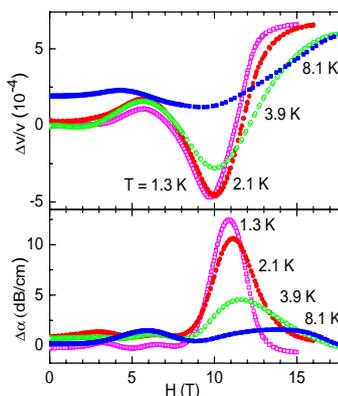


Fig. 3: Relative change of sound velocity and attenuation of the c_{33} -mode at 78 MHz as a function of magnetic field parallel to the c axis for $T > T_N^{\text{max}}$.

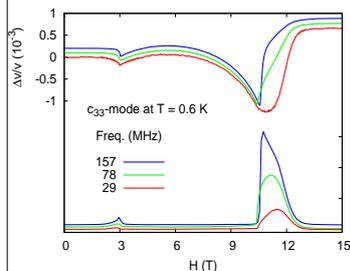


Fig. 4: Relative change of sound velocity and attenuation of the c_{33} -mode at 78 MHz, at $T = 0.6$ K and for three frequencies: 29, 78, and 157 MHz. The curves are vertically offset for clarity.

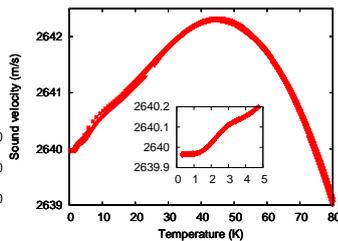


Fig. 5: Sound velocity of the c_{33} -mode at -78 MHz in DTN as a function of temperature. Data were obtained in two different crystals.

Discussion

- Strong spin-lattice interaction was observed both in the disordered and ordered phases (Fig. 2 and 3).
- Strong frequency dependence of anomalies in the critical region was observed (Fig. 4).
- The anomalies allow to map the phase diagram, which is in agreement with results from Ref. [2] and [3] (Fig. 1).
- The sound velocity shows a maximum at ~ 44 K (Fig. 5).

- The spin-phonon interaction can be explained in terms of exchange striction.
- The effective free-fermion theory yields a good qualitative description for the behavior of the sound velocity and attenuation [5]. (Fig. 6)
- The frequency dependence in the critical regions indicates that relaxation processes are relevant.

Theory

- Effective free-fermion theory was applied to the 1D $S = 1$ spin chain in the gaped regime.

- E.g., the sound velocity change reads as

$$v_l = \frac{A_1 + A_2}{(N\omega_s)^2}$$

$$A_1 = 2 |g_q(k)|^2 \langle S_0^z \rangle^2 \chi_0^\alpha + T \sum_q \sum_{\alpha=x,y,z} |g_q^\alpha(k)|^2 (\chi_q^\alpha)^2$$

$$A_2 = |h_q(k)|^2 \langle S_0^z \rangle^2 + \frac{T}{2} \sum_q \sum_{\alpha=x,y,z} |h_q^\alpha(k)|^2 (\chi_q^\alpha)^2$$

where g_q^α and h_q^α - spin-phonon coupling constants;

$\chi_q^\alpha = \chi_q^{\alpha(1)} / [1 - ZJ_{ab}\chi_q^{\alpha(1)}]$ - magnetic susceptibility with Z - the coordination number, $\chi_q^{\alpha(1)}$ - susceptibility of 1 chain

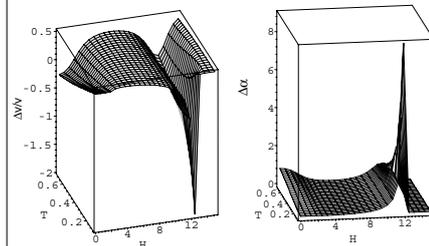


Fig. 6: Relative change of velocity (left) and attenuation (right) of longitudinal sound as a function of temperature and magnetic field, calculated within the framework of the effective free-fermion theory.

Conclusions

- There is a strong spin-phonon interaction in DTN.
- The sound velocity and the attenuation are renormalized in the vicinity of the quantum critical points.
- The (H, T) phase diagram was determined with high accuracy.

Outlook

- Clarify the origin of the sound-velocity maximum at ~ 44 K.
- Analysis of the relaxation processes in the critical region

References

- Paduan-Filho *et al.*, *Phys. Rev. B* **69**, 020405R (2004)
- Zapf *et al.*, *Phys. Rev. Lett.* **96**, 077204 (2006)
- Zvyagin *et al.*, *Phys. Rev. Lett.* **98**, 047205 (2007)
- Zapf *et al.*, *Phys. Rev. B* **77**, 020404R (2008)
- Chiatti *et al.* (submitted to *Phys. Rev. Lett.*)

Experimental details

- We use a phase-sensitive detection technique based on a standard ultrasonic pulse-echo method.
- The relative changes of the velocity and attenuation of longitudinal sound waves propagating along the c axis (c_{33} -mode) are measured as a function of temperature T and external magnetic field H (applied along the c axis).
- Absolute measurements of the sound velocity at room temperature and at low temperatures were performed for different frequencies.

